

Manuscript Number: CCC-D-14-00528R1

Title: Influence of calcium aluminate cement (CAC) on alkaline activation of red clay brick waste (RCBW)

Article Type: Research Paper

Keywords: Ceramic waste; Waste management; Alkali-Activation; Calcium aluminate cement; Compressive strength

Corresponding Author: Mrs. Lucia Reig, Ph.D.

Corresponding Author's Institution: Universitat Jaume I

First Author: Lucia Reig, Ph.D.

Order of Authors: Lucia Reig, Ph.D.; Lourdes Soriano, PhD; María V Borrachero; José Monzó; Jordi Payá

Abstract: In this paper, the effect of calcium aluminate cement (CAC) additions on the alkali activation of red clay brick waste (RCBW) was studied at room temperature and at 65 °C. RCBW was partially replaced with CAC (0 to 50 wt.%) and blends were activated with NaOH and sodium silicate solutions. The compressive strength evolution was tested on mortars and the nature of the reaction products was analysed by infrared spectroscopy, X-ray diffraction, thermogravimetric analysis, microscopic studies and pH measurements. The results show that the use of CAC accelerates the activation process of RCBW so that 50 MPa were obtained in the blended mortars containing 40 wt.% CAC cured for 3 days at room temperature. CAC did not undergo normal hydration and only the C3AH6 phase was identified in the pastes blended with more than 30 wt.% CAC and cured at 65°C, while the main reaction product was a cementitious gel containing Ca and Al from CAC.

**Influence of calcium aluminate cement (CAC) on alkaline activation
of red clay brick waste (RCBW)**

L. Reig ^a, L. Soriano ^b, M.V. Borrachero ^b, J. Monzó ^b, J. Payá ^b

^a EMC, Universitat Jaume I, Av. Sos Baynat s/n 12071 Castelló de la Plana, Spain.

^b Instituto de Ciencia y Tecnología del Hormigón (ICITECH), Universitat Politècnica de València,
Camino de Vera s/n 46022 Valencia, Spain.

Corresponding author: L. Reig; lreig@uji.es

Tel.: +34 964 729163

Fax: +34 964 728106

E-mail addresses: lreig@uji.es; lousomar@gmail.com; vborrachero@cst.upv.es;

jmmonzo@cst.upv.es; jjpaya@cst.upv.es

Abstract

1
2
3
4
5
6 In this paper, the effect of calcium aluminate cement (CAC) additions on the alkali activation of
7 red clay brick waste (RCBW) was studied at room temperature and at 65 °C. RCBW was
8 partially replaced with CAC (0 to 50 wt.%) and blends were activated with NaOH and sodium
9 silicate solutions. The compressive strength evolution was tested on mortars and the nature of
10 the reaction products was analysed by infrared spectroscopy, X-ray diffraction,
11 thermogravimetric analysis, microscopic studies and pH measurements. The results show that
12 the use of CAC accelerates the activation process of RCBW so that 50 MPa were obtained in
13 the blended mortars containing 40 wt.% CAC cured for 3 days at room temperature. CAC did
14 not undergo normal hydration and only the C_3AH_6 phase was identified in the pastes blended
15 with more than 30 wt.% CAC and cured at 65°C, while the main reaction product was a
16 cementitious gel containing Ca and Al from CAC.
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31

Keywords:

32 Ceramic waste

33 Waste management

34 Alkali-Activation

35 Calcium aluminate cement

36 Compressive strength

37 Microstructure
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1. Introduction

Portland cement is the dominant binder used in concrete. However, the large amounts of energy and greenhouse gases emitted to the atmosphere during its production process have prompted the scientific community to propose different alternatives to reduce its environmental impact. As reviewed by Juenger et al. [1], alkali-activated binders are receiving more attention from among the different alternatives proposed, which is attributed to their excellent strength, durability and low environmental impact. Furthermore in this methodology, the solid material to be activated may be entirely (or almost entirely) composed of waste materials [1]. As described by Shi et al. [2], during the alkali-activation process, a solid silico-aluminous material is mixed with a highly concentrated alkali solution. The resulting paste is an aluminosilicate hydrate that has a three-dimensional structure, with both Al and Si tetrahedrally coordinated, and the alkali (Na or K) located in the voids of this framework, which compensate for electric charges.

A wide variety of industrial by-products and waste materials have been successfully activated by the scientific community [2-5], some of which are ceramics. Among them, Puertas et al. [6] achieved 13 MPa (compression) by the alkali activation of different types of ceramic tiles, cured at 85°C for 24h and at 20°C for 7 days. Payá et al. [7] also developed mortars with compressive strength values above 10 MPa by the activation of hydrated-carbonated cement cured at 65°C. Porcelain stoneware tiles were activated by Reig et al. [8], where the addition of $\text{Ca}(\text{OH})_2$ proved essential to obtain mortar samples with up to 36 MPa under compression (7 days at 65°C). Red clay brick waste has also been activated in a previous research work [9], where up to 50 MPa were reported under compression in mortars cured at 65°C for 7 days. Although the development of binders by the alkali activation of ceramic materials has been extensively proved, what most of these studies have in common is that curing at high temperature was required for the activation process to take place.

1 In the works by Fernandez-Jimenez et al. [10] and Arbi et al. [11], calcium aluminate cement
 2 (CAC) was added to the system as a source of calcium and reactive alumina. Thus compressive
 3 strength values close to 13 MPa were obtained in the alkali-activated metakaolin pastes
 4 containing 20% CAC (cured at 85°C for 20 h) [10]. Even higher compressive strength values
 5 (23.7 MPa) were achieved in [11] by the activation of blast furnace slag and CAC blends (80 to
 6 20 wt.%) cured at room temperature for 2 days. Thus although CAC production consumes
 7 natural resources (bauxite and limestone), emits CO₂ to the atmosphere and requires energy to
 8 reach clinkering temperatures, moderate amounts of this cement may improve the behaviour
 9 and properties of the blended system. As Pacewska et al. [12] described, CAC is a hydraulic
 10 binder with special properties, such as rapid strength gain, good durability in high sulphate
 11 environments, resistance to fire, chemical attack and abrasion. Monocalcium aluminate (CA) is
 12 the principal active phase in CAC cement, which reacts with water to give calcium aluminate
 13 hydrates. As described by Juenger et al. [1], hydration temperature is one of the most significant
 14 parameters to influence the phases that are formed and the transition rate from metaestable to
 15 stable hydrates (conversion process). Whereas CA hydrates at environmental temperatures (15
 16 to 25°C) to give hexagonal phases CaAl₂O₄·10H₂O (CAH₁₀) and Ca₂Al₂O₅·8H₂O (C₂AH₈), with
 17 an increased quantity of C₂AH₈ with rising temperature, curing within the 25-40°C range yields
 18 C₂AH₈ as the main hydration product, together with alumina gel, which crystallizes with time to
 19 gibbsite Al(OH)₃ (AH₃). When temperature rises above 40°C, and especially up to 60°C, phase
 20 Ca₃Al₂(OH)₁₂ (C₃AH₆) is formed (cubic phase), together with hydrous alumina, which gradually
 21 changes to gibbsite. As extensively proved by the scientific community [1,13,14], CAH₁₀ and
 22 C₂AH₈ are metastable products that inevitably convert into stable C₃AH₆ and AH₃ phases
 23 depending on time, temperature, humidity or pH. The conversion of these metastable hydrates
 24 into the stable cubic phase occurs in accordance with Equations (1) and (2) [13], and is
 25 accompanied by AH₃ gel formation and the release of water (H). As a result, the porosity of the
 26 paste increases, and the strength of the material subsequently diminishes [1,13-15].
 27
 28
 29
 30
 31
 32
 33
 34
 35
 36
 37
 38
 39
 40
 41
 42
 43
 44
 45
 46
 47
 48
 49
 50
 51
 52
 53
 54
 55
 56
 57
 58
 59
 60
 61
 62
 63
 64
 65



1 Carbonation of CAC hydrates may also occur if CO_2 from the atmosphere is absorbed, which
2 results in the formation of CaCO_3 and AH_3 . As explained in [14], the hexagonal phases
3 carbonate faster than the cubic one as they are less stable and dissolve CO_2 more easily. The
4 alkaline hydrolysis, a durability problem associated with CAC, has been described in [14] also
5 as a carbonation process which occurs with high pH values and in the presence of alkalis, and
6 which destroys the hexagonal and cubic hydrates that confer cementitious properties to the
7 binder. In this process, the carbonated alkalis (Na_2CO_3) formed by the combination of NaOH
8 and CO_2 react with the hydrated calcium aluminates (CAH_{10} , C_2AH_8 , C_3AH_6) to form soluble
9 alkali aluminates.
10
11
12
13
14
15
16
17
18
19
20
21
22
23

24 The scientific community has been seeking alternatives to mitigate the durability problems
25 associated with CAC cements (conversion, carbonation and alkaline hydrolysis). Authors such
26 as Pacewska et al. [16] and Hidalgo et al. [13] introduced into the cement system appropriate
27 additions of spent catalyst FCC [16], and silica fume or fly ash [13] to stabilise CAC hydrates
28 and to avoid, or to at least reduce, their conversion and negative effects on CAC composites.
29 An alternative reaction for metastable hydrates was observed in both the above studies, with
30 silicate ions reacting with calcium aluminate hydrates ($\text{CAH}_{10}\text{-C}_2\text{AH}_8$) to form Strätlingite
31 (C_2ASH_8), a stable hydrate formed within the normal temperature range. In [10], metakaolin and
32 CAC blends were alkali-activated with NaOH and sodium silicate solutions. None of the
33 compounds normally observed in water-hydrated CAC (CAH_{10} , C_2AH_8 , C_3AH_6 , AH_3) was
34 detected under the study conditions (curing at 85°C for 2 or 20 h), and the Al and Ca from CAC
35 were taken up in the aluminosilicate gel formed in the activation process. Through the hydration
36 of CAC with NaOH solutions, Pastor et al. [17] also found that alkali activation accelerated the
37 conversion process to yield the cubic aluminate hydrate from very early ages (2 days in
38 samples activated with 8 M and 12 M NaOH), instead of the hexagonal aluminates (CAH_{10} and
39 C_2AH_8) that appeared during standard water hydration. These results have been corroborated in
40 [18] by CAC hydration with highly alkaline NaOH (8M) and sodium silicate solutions, where
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 high pH values resulted in the formation of cubic hydrates from the outset, and no C_2ASH_8 was
2 formed since silicon was taken up to form katoite-type phases ($C_3AS_nH_m$).
3
4

5 The work reported herein aims to understand the influence of calcium aluminate cement (CAC)
6 additions and curing temperature on the mechanical strength and microstructure evolution of
7 alkali-activated red clay brick waste (RCBW) cements. RCBW was partially replaced with CAC
8 (0 to 50 wt.%), and blends were activated with NaOH/sodium silicate solutions and cured at
9 room temperature and at 65°C. .
10
11
12
13
14
15
16
17
18
19

20 **2. Experimental Procedure**

21 *2.1. Materials*

22
23
24
25
26
27
28
29
30
31
32 The studied samples were prepared with red clay brick waste (RCBW) and calcium aluminate
33 cement (CAC), the latter produced by the company Cementos Molins S.A. (Barcelona, Spain).
34 Red clay bricks were crushed in a jaw crusher (BB200, Retsch) to obtain a granular material
35 with a particle size of less than 4 mm. This was then dry-milled in alumina media for 40 minutes,
36 and powder with a mean particle size close to 21 μm and 90 vol.% less than 56.2 μm was
37 obtained (determined by laser diffraction in a Mastersizer 2000, Malvern Instruments). The CAC
38 particle size was similar, with a mean diameter of 27.7 μm and 90 vol.% under 64.3 μm .
39
40
41
42
43
44
45
46 According to the SEM images in Fig. 1, both RCBW and CAC particles were irregularly shaped.
47
48
49
50
51

52 The chemical composition of RCBW and CAC, determined by X-ray fluorescence (XRF, Philips
53 Magix Pro), is provided in Table I. While CAC is composed mainly of Al_2O_3 and CaO, RCBW
54 contains high levels of SiO_2 and Al_2O_3 , which are essential for the alkali-activation process. The
55 amorphous content of RCBW, determined following UNE EN 196-2, was around 35%.
56
57
58
59
60
61
62
63
64
65

Table 1. Chemical composition of raw materials, wt. %

Oxide	RCBW	CAC
SiO ₂	49.9	4.9
Al ₂ O ₃	16.6	37.1
Fe ₂ O ₃	6.5	15.6
CaO	9.7	35.4
MgO	5.5	1.3
Na ₂ O	0.5	0.6
TiO ₂	0.8	2.4
SO ₃	3.3	0.7
K ₂ O	4.4	0.7
Other	0.4	0.3
LOI	2.4	1.0

2.2. Matrix Preparation

Different percentages of calcium aluminate cement (0 to 50 wt.%) were used to substitute ceramic waste. The alkali-activating solutions were prepared by mixing sodium hydroxide pellets (98% purity, Panreac), water and sodium silicate (Merck, SiO₂=28%, Na₂O=8%, H₂O=64%). The activating solution dosage (SiO₂/Na₂O molar ratio of 1.60) was adopted from previous studies [9] and was kept constant for all the pastes and mortars mixed. A water to binder ratio (w/b) of 0.40 was used in the present research, which was lower than that previously reported in [9] due to the better workability of the RCBW-CAC blended mortars. A water-hydrated CAC paste (w/b 0.35) was prepared for comparison.

Pastes and mortars were produced according to the process previously described in [9,19]. They were cured in a thermostatically-controlled bath at 65°C at a relative humidity (RH) of 96% for 3 and 7 days; and in a room temperature chamber (20°C, RH 96%) for 3, 7, 14 and 28 days. A sand to binder (sum of CAC plus RCBW) ratio of 3:1 was used for all the prepared mortars. The process variables used in this study are summarised in Table 2.

Table 2. Dosages and curing conditions of pastes and mortars

RCBW wt.%	CAC wt.%	w/b	SiO ₂ /Na ₂ O molar ratio	Sand/binder	Curing conditions
100	0				
90	10				
80	20	0.40	1.60	3:1	3 and 7 days 65°C
70	30				
60	40				
50	50				
100	0				
90	10				
80	20	0.40	1.60	3:1	3, 7, 14 and 28 days 20°C
70	30				
60	40				
50	50				
0	100	0.35	-	-	

2.3. Characterisation

The compressive strengths of the alkali-activated mortars were determined following UNE EN 196-1 using 160 x 40 x 40 mm samples. Pastes were used to assess the microstructure evolution of the developed samples. Thermogravimetry tests (TG, 850 Mettler-Toledo) were run in sealed pin-holed aluminium crucibles at a heating rate of 10°C min⁻¹, from 35°C to 600°C, in an N₂ atmosphere. X-ray diffraction tests (XRD, Brucker AXS D8 Advance) were run from 5° to 55° 2θ degrees, with Cu Kα radiation at 40 kv and 20 mA. The Fourier-transformed infrared spectroscopy (FTIR, Bruker Tensor 27 Platinum ATR spectrometer) data were collected in the transmittance mode, from 4,000 to 400 cm⁻¹. Water/binder suspensions were monitored by

1 electrical conductivity and pH measurements (microCM2201 conductimeter and microPH2001
2 pH-meter by Crison). These analyses were performed by dissolving 1g of paste with 10 ml of
3 distilled water for 10 min. Data were taken from 1 day up to the maximum curing age
4 established in the present study (28 days at 20°C and 7 days at 65°C). The microstructure of
5 the alkali-activated RCBW-CAC paste samples was examined using SEM–EDX (JEOL JSM-
6 6300).
7
8
9
10

11 **3. Results and Discussion**

12 13 14 15 16 17 18 *3.1. Mechanical Strength*

19
20
21
22
23
24
25 The evolution of the compressive strength of the alkali-activated RCBW-CAC blended mortars,
26 cured at room temperature and at 65°C for different periods of time is depicted in Fig. 2. The
27 mortars with 50 wt.% CAC did not develop since rapid setting occurred in the preparation
28 process. The alkali-activated RCBW mortar with no CAC addition required high temperature
29 curing conditions to initiate the chemical reactions associated with the alkali-activation process.
30 While only 10 MPa were achieved after 28 curing days at room temperature, this value
31 increased up to 35 MPa after curing at 65°C for 7 days. Conversely, although the mortars cured
32 at 65°C always exhibited higher compressive strength values than that cured at room
33 temperature, the mechanical properties of that containing CAC were similar after 28 days at
34 20°C or 7 days at 65°C, no matter what the CAC addition.
35
36
37
38
39
40
41
42
43
44
45
46
47
48

49 The mechanical properties of all the prepared mortars increased with CAC addition. Although
50 the kinetics of the room temperature process was quite slow for the samples containing 10 wt.%
51 CAC (\approx 15 MPa, 7 curing days), more than 30 MPa were achieved after 28 curing days.
52
53 Increasing CAC content to 20 wt.% significantly improved compressive strength, with 38 MPa
54 and 55 MPa being achieved after 7 and 28 curing days, respectively. The values obtained for
55 the greatest CAC additions (40 wt.%) came close to 80 MPa (28 days at 20°C), which fall within
56
57
58
59
60
61
62
63
64
65

1 the range previously reported by Fernandez-Jimenez et al. [18] and Pastor et al. [17] in alkali-
2 hydrated CAC pastes activated with 8M NaOH solutions and cured at room temperature for 28
3 days. Increased strength with curing time was also observed in both studies [17,18], which is in
4 good agreement with the obtained results.
5
6

7 8 9 10 *3.2. Evolution of pH and electrical conductivity*

11
12
13
14 The reaction processes of the developed samples were monitored by electrical conductivity and
15 pH measurements. Pastes were dissolved in distilled water for 10 minutes, and data were
16 collected every 4 h on curing day 1 and at the different curing ages, established to assess
17 compressive strength evolution (3 and 7 days at 65°C; 3, 7, 14 and 28 days at room
18 temperature). Fresh RCBW-CAC samples showed an initial electrical conductivity of 18.1-20.3
19 mS/cm. These values significantly decreased after 3 curing days to yield values within the range
20 of 14.3-17.8 mS/cm at 20°C, and 9.8-12.6 mS/cm at 65°C. In general, the values of the
21 activated pastes cured at room temperature were slightly higher than those cured at 65°C for all
22 the testing ages, which is attributed to the slower reactivity of the pastes cured at room
23 temperature. From 3 to 28 days curing days at 20°C, electrical conductivity decreased to the
24 11.1-14.2 mS/cm range, suggesting a continuous reaction in these systems. Generally, the
25 electrical conductivity values found for the highest CAC content samples (30 wt.% and 50 wt.%)
26 were slightly higher than those found for that containing 0 wt.% and 10 wt.% CAC. However, the
27 differences between the RCBW paste (0 wt.% of CAC) and that containing 50 wt.% CAC were
28 not significant, which suggests that the alkali solution reacted with both materials (ceramic
29 waste and cement). According to Tashima et al. [3], the lower conductivity observed with curing
30 time is attributed to the chemical combination of Na⁺, OH⁻ groups and silicate anions while the
31 alkali-activated matrix formed. Furthermore, CAC probably reacted with a smaller quantity of
32 ions in the activating solution to leave more ions in the pore solution. Water-hydrated CAC
33 cement exhibited the lowest electrical conductivity values (2.57 mS/cm in fresh state, which
34 lowered to 1.57 mS/cm after 24 h of curing at room temperature), and slightly reduced to 1.42
35 mS/cm after 28 curing days.
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 Alkali-activated CAC blended pastes presented pH values that ranged from 12.3 to 12.8. The
2 data collected immediately after the mixing process (12.8 for 50 wt.% CAC and 12.6 for 0 wt.%
3 CAC) gave slightly lower values with curing time, which ranged from 12.6 (50 wt.% CAC) to 12.3
4 (0 wt.% CAC) after 28 curing days at 20°C or 7 days at 65°C. Similarly to the electrical
5 conductivity behaviour, the water-hydrated CAC paste obtained the lowest pH values, which
6 went 11.8 right immediately being mixed, to 11.5 after 28 curing days at 20°C. As previously
7 observed in the studies by Pastor et al. and Shi et al. [2,17], high pH values slow down the
8 dissolution rate of Ca and accelerate that of Al and Si, which influences the developed
9 microstructure. Yet according to Garcia Lodeiro et al. [20], the presence of calcium also
10 modifies the structure of N-A-S-H gels by replacing part of the sodium with calcium to form
11 (N,C)-A-S-H gels. The stability of these structures in the presence of calcium depends heavily
12 on pH; thus if sufficient calcium is provided, pH values of over 12 promote the formation of C-A-
13 S-H rather than N-A-S-H gel.

30 3.3. Infrared spectroscopy (FTIR)

31
32
33
34
35
36
37 The FTIR curves of the alkali-activated RCBW-CAC blends, cured at 20°C for 28 days and at
38 65°C for 7 days, are plotted in Fig. 3a and 3b, respectively. The spectrum of the water-hydrated
39 CAC paste, cured at room temperature, is also presented for comparison purposes. The
40 presence of quartz, also identified by XRD (Section 3.4), was corroborated in all the RCBW-
41 containing samples, and was associated with the signals appearing at 460 cm⁻¹, 668 cm⁻¹, 697
42 cm⁻¹, 796-778 (double band) cm⁻¹, 1084 cm⁻¹ and 1150 cm⁻¹ [21,22], with decreasing intensity
43 with higher CAC additions.

44
45
46
47
48
49
50
51
52
53
54
55 The FTIR spectra may be difficult to identify since bands attributed to different compounds tend
56 to overlap. As reported in [16,17,21,23], the bands attributed to AH₃ appear at 3475, 3530 and
57 3630 cm⁻¹ (O-H stretching vibration) and in the 1027 and 990-970 cm⁻¹ region (O-H bending
58
59
60
61
62
63
64
65

1 vibration), and overlap that typical of CAC hydrates and the newly formed aluminosilicate gel,
2 respectively. As explained in [17,21], the high frequency bands of CAH_{10} (3500 cm^{-1}), C_2AH_8
3 and C_3AH_6 (narrow band at 3665 cm^{-1}) hydrates also overlap since they present very similar
4 spectra [21,24]. The signals appearing at 3465 , 3525 and 3620 cm^{-1} in the water-hydrated CAC
5 paste, whose intensity increased with curing time, are attributed to both gibbsite and CAC
6 hydrates. The bands assigned typically to CAC hydrates (CAH_{10} , C_2AH_8 and C_3AH_6), which
7 appear at 524 cm^{-1} and in the $3465 - 3670\text{ cm}^{-1}$ region [24], were not clearly distinguished by the
8 FTIR analyses in the alkali-activated RCBW-CAC samples. Only a slight tendency within the
9 $3,200$ to $3,600\text{ cm}^{-1}$ range was observed with increasing CAC additions, which implies that no
10 significant amounts of these hydrates were formed. The results are in good agreement with
11 those reported by Shi et al. [2], who stated that when less than 30% CAC is used in alkali-
12 activated calcium aluminate-blended cements, CAC does not undergo normal hydration, and no
13 cubic, hexagonal hydrates or $\text{Al}(\text{OH})_3$ are observed since Al and Ca of CAC are taken up in the
14 (C,N)-A-S-H gel formed. Pastor et al. [17] and Fernandez-Jimenez et al.[18], who activated
15 CAC, also observed that highly alkaline solutions expedite the conversion from hexagonal into
16 cubic hydrates, which results in katoite formation (C_3AH_6) from the outset.

17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36 Several papers [13,16,18] have also addressed CAC hydration with water in the presence of
37 reactive silica-rich compounds (slag, silica fume, fly ash, etc.). Most of these papers reported
38 that metaestable calcium aluminates (CAH_{10} and C_2AH_8) react with added silica to form
39 strätlingite (C_2ASH_8), a stable crystalline hydrate that inhibits or retards the conversion from
40 hexagonal into cubic hydrates [18]. However, FTIR or XRD analyses in the present study
41 detected no strätlingite, which is attributed to the fact that no significant amounts of typical CAC
42 hydrates formed in the activated samples. These results are also in good agreement with those
43 previously reported by Fernandez-Jimenez et al. [18], who did not observe C_2ASH_8 formation
44 when activating CAC in highly alkaline solutions and in the presence of soluble silica. According
45 to [18], these conditions favour the reaction between the silica and aluminum and calcium in
46 CAC to produce a sodium and calcium aluminosilicate hydrate (C,N-A-S-H) gel, which may
47 crystallise into zeolitic phases. These authors also found that silicon is taken up to form katoite-

1 type phases ($C_3AS_nH_m$). However, the main bands attributed to $C_3AS_3-xH_{2x}$ solid solution
2 hydrates are difficult to identify by FTIR tests since, as reported by Hidalgo et al. [13], they
3 occur at 3,660, 900 and 550 cm^{-1} , and overlap that of typical CAC hydration products and the
4 newly-formed gel.
5
6
7
8
9

10
11 All the alkali-activated samples showed a broad band centred at $\approx 1,000\text{ cm}^{-1}$, which has been
12 attributed to the vibrations of the Si–O–T (T = Al, Si) bonds in the newly formed aluminosilicate
13 gel [18]. A slight deviation towards lower wave numbers with increasing CAC contents was
14 observed, which indicates more Al contents [21,25]. The signal that appears in the 460 cm^{-1}
15 region also slightly shifted towards lower wave numbers with more CAC additions. Although this
16 signal is attributed mainly to quartz, bands due to the deformation vibrations of C-A-S-H and N-
17 A-S-H gels (δ Si-O-Si / δ Si-O-Al) also appear in this region [26]. As explained by García-
18 Lodeiro et al. [26,27], the type and characteristics of the formed gel are conditioned clearly by
19 the working pH and the calcium concentration in the system. Thus even in the presence of Ca,
20 N-A-S-H persists with pH values below 12, and by accepting Ca by an ion exchange
21 mechanism to confer (N,C)-A-S-H until all the Na has been replaced with Ca (if sufficient Ca is
22 available). However, pH values of over 12 favour the formation of a C-A-S-H rather than a N-A-
23 S-H gel, given that sufficient calcium is provided. According to Juenger et al. [1], while the C-
24 (A)-S-H gel is amorphous to partially crystalline, the geopolymer-type gel N-A-S-H is a highly
25 cross-linked aluminosilicate gel that strongly resembles zeolite frameworks nanostructurally and
26 is generally lacking in the long-range crystalline order. Garcia-Lodeiro et al. [20] also agreed
27 that the alkaline activation of low calcium materials, such as metakaolin, leads to N-A-S-H gel
28 precipitation, which provides zeolites such as hydroxysodalite, zeolite P, Na-chabazite, zeolite Y
29 or faujasite as secondary reaction products. These observations, together with the fact that no
30 significant amounts of zeolitic-type products were clearly distinguished by the XRD or FTIR
31 analyses in RCBW-CAC blended systems (characteristic bands at 660 and 720 cm^{-1} [28]), led to
32 the conclusion that (N,C)-A-S-H rather than a N-A-S-H gel is being formed, with increasing C-A-
33 S-H contents if there are more CAC additions.
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 According to [16,22,24], the bands appearing from 1,415 cm⁻¹ to 1,600 cm⁻¹ are associated with
2 the stretching vibrations of CO₃²⁻ in carbonates. The intensity of these bands was higher in the
3 pastes cured at room temperature than that cured at 65°C. While calcite-type bands appear at
4 lower wave numbers (1420 cm⁻¹), that of carbonate impurity species shift to higher values
5 (Natriite, Na₂CO₃, 1,455 cm⁻¹; vaterite, 1,484 cm⁻¹ [17]), which denotes higher calcite-type
6 compounds with increasing CAC additions. The absorption bands at 712 and 875 cm⁻¹, when
7 connected with the distinct bands at about 1,420 cm⁻¹, are also related to carbonate salts [16].
8 Pastor et al. [17] observed an increasing intensity of the bands attributed to carbonates with
9 curing time in alkali-activated CAC, together with increasing AH₃ contents and a decline in the
10 C₃AH₆ hydrate. It was not possible to corroborate this evolution by FTIR analyses in the present
11 study since the signals attributed to both AH₃ and CAC hydrates overlapped in the 3,200 to
12 3,600 cm⁻¹ region, and they did not vary significantly with curing time. The signals attributed to
13 hydrated calcium monocarboaluminate 3CaO·Al₂O₃·CaCO₃·11H₂O, a metastable intermediate
14 specie in the carbonation process identified by XRD analyses, also appeared in the 3,760 cm⁻¹
15 region [13], which is difficult to identify by FTIR. Although the formation of further calcite
16 contents with CAC addition may be linked to the alkaline hydrolysis process, no significant
17 amounts of typical CAC hydrates were identified by FTIR or XRD analyses, especially in the
18 samples containing up to 10 wt.% CAC. During alkaline hydrolysis, the hydrated calcium
19 aluminates react with carbonated alkalis (Na₂CO₃) to give CaCO₃ and soluble alkaline aluminate
20 Na₂O·Al₂O₃ [14]. This aluminate reacts with water and renders new alkaline hydroxides that
21 maintain the CAC hydrates destruction process.

22 3.4. X-ray diffraction (XRD)

23 The results of XRD analyses obtained for the pastes cured at 20°C for 28 days and at 65°C for
24 7 days are presented in Fig. 4a and 4b, respectively. The RCBW diffractogram is plotted for
25 comparison purposes. The data show that quartz (SiO₂, PDFcard331161) is the major
26 crystalline phase to appear in the raw material, with the calcium silicate rankinite (2SiO₂·3CaO,
27 PDFcard220539), and the feldspars albite (NaAlSi₃O₈, PDFcard090466) and microcline

1 (KAlSi₃O₈, PDFcard090466) present as minor constituents. Typical CAC hydrates (CAH₁₀,
2 C₂AH₈ and C₃AH₆), together with the crystalline phase gibbsite (AH₃), were clearly identified in
3 the water-hydrated CAC paste. This sample also contained unreacted clinker phases of cement,
4 type monocalcium aluminate (CaO·Al₂O₃, PDFcard231036) and small amounts of
5 carboaluminate phase Ca₄Al₂O₆CO₃·11H₂O (PDFcard410219).
6
7
8
9
10

11
12
13 The signals attributed to quartz appeared in all the samples containing RCBW, with decreasing
14 intensity if CAC contents increased, due to the dilution effect in the RCBW-CAC systems. A
15 deviation from the baseline within the 20 to 35 2θ degrees range was observed in all the alkali-
16 activated samples, which augmented with CAC addition and denotes the further development of
17 amorphous phases. Only the crystalline phases that were attributed to the raw material were
18 clearly identified in the pastes containing up to 10 wt.% CAC and cured at 20°C. Monocalcium
19 aluminate was observed with increasing CAC contents (30 and 50 wt.%, cured at 20°C),
20 together with minor amounts of carboaluminate phase aluminohydrocalcite
21 (CaAl₂(CO₃)₂(OH)₄·3H₂O, PDFcard220138), whose signals intensified with CAC addition.
22
23
24
25
26
27
28
29
30
31
32
33

34
35
36 The XRD spectra of the alkali-activated pastes blended with 0 wt.% and 10 wt.% CAC cured at
37 65°C were similar to that cured at room temperature. Although zeolitic phase Herschelite
38 (NaAlSi₂O₆·3H₂O, PDFcard191178) was identified in the paste mixed with 10 wt.% CAC, it
39 disappeared with increasing CAC contents (30 and 50 wt.%), and minor amounts of cubic phase
40 katoite (C₃AH₆, PDFcard240217) appeared with a higher intensity with CAC addition. Minor
41 amounts of AH₃ polymorph bayerite (PDFcard200011), together with the formation of a new
42 hydrated calcium silicoaluminate crystalline phase (Ca₆(AlSiO₄)₁₂·30H₂O, PDFcard110589),
43 were formed in the paste containing 50 wt.% CAC.
44
45
46
47
48
49
50
51
52
53

54
55
56 The X-ray results are in good agreement with those obtained in the FTIR and TG analyses
57 since no crystalline gibbsite or hexagonal hydrates were clearly identified in the alkali-activated
58 RCBW-CAC blended samples, and the phase bayerite was only observed in the paste
59
60
61
62
63
64
65

1 containing 50 wt.% CAC and cured at 65°C for 7 days. Cubic phase katoite (C_3AH_6) was
2 detected only in the pastes blended with high CAC contents (30 wt.% and 50 wt.%) cured at
3 65°C. The results are in accordance with the previous review by Shi et al. [2], which pointed out
4 that alkali-activated CAC blended cements do not undergo normal hydration and, instead of
5 cubic or hexagonal typical CAC hydrates being formed, Al and Ca were taken up in the N-A-S-H
6 gel to confer (N,C)-A-S-H or C-A-S-H gels depending on the blend proportions and reaction
7 conditions. Pastor et al. [17] also detected an alternative reaction form in the NaOH-hydrated
8 CAC samples, which led to the formation of cubic hydrate C_3AH_6 and AH_3 instead of hexagonal
9 aluminates (CAH_{10} and C_2AH_8), which usually appear during standard water hydration. Neither
10 were hexagonal hydrates found in the study by Fernandez Jimenez et al. [18], where CAC was
11 hydrated in NaOH and sodium silicate solutions. While cubic phase C_3AH_6 was identified in the
12 alkali-activated pastes with no silica addition, presence of this compound was found to interact
13 with C_3AH_6 to form $Ca_{2.93}Al_{1.97}(Si_{0.64}O_{2.56})(OH)_{9.44}$ and the calcium aluminum silicate hydrate,
14 known as Linde A ($Ca_6(AlSiO_4)_{12} \cdot 30H_2O$, ICDD-11-0589) [18], which was also identified by the
15 XRD tests in the paste developed in the present research work blended with 50 wt.% CAC and
16 cured at 65°C for 7 days.

36 3.5. Thermal analysis (DTA/TG)

37
38
39
40
41
42 The differential thermogravimetric curves (DTG) of the alkali-activated RCBW-CAC blends,
43 cured at 20°C for 28 days and at 65°C for 7 days are plotted in Fig. 5a and 5b, respectively.
44 Total weight loss generally increased with CAC addition and curing time, and ranged from 7.4
45 wt.% to 9.0 wt.% in the pastes cured for 3 days at 20°C (0 wt.% and 50 wt.% CAC,
46 respectively), up to 8.9 wt.% (0 wt.% CAC) to 11.7 wt.% (50 wt.% CAC) in those cured for 28
47 days. Values were slightly higher in the pastes cured at 65°C for 7 days (10.2 wt.% in 0 wt.%
48 CAC to 12.5 wt.% in 50 wt.% CAC), which is attributed to faster reaction progress. These results
49 are in good agreement with compressive strength evolution.

A water-hydrated CAC paste, cured at room temperature, was tested for comparison purposes.

While the first peak appearing on the DTG curve (130 °C), which is associated with the dehydration of the C-A-H and alumina gel [23,26], increased with curing time, the second one (150°C to 180°C), which corresponds to the dehydration of CAH_{10} and C_2AH_8 [16,23], was maximum after 14 curing days, but decreased afterwards, indicating that the conversion process occurred. The bands that appeared within the 180-220°C range, whose intensity increased with curing time, are associated with the dehydration of carboaluminate phases and further C_2AH_8 dehydration. The intensity of the signal due to the dehydration of gibbsite AH_3 (309 °C) [16,23] also increased with curing time, and that associated with C_3AH_6 cubic compounds (≈ 340 °C) [16] appeared after 7 curing days and increased to 28 days.

The thermogravimetric curves of the alkali-activated pastes with no CAC or with 10 wt.% addition exhibited a single broad band centred at 140-160°C which, according to Tashima et al. [3], is attributed to the dehydration of the newly-formed gel, originated by loss of water molecules and/or OH^- groups from the products formed in the alkali-activation process. Zeolitic phase Herschelite, which was previously identified by the XRD tests in the pastes blended with 10 wt.% CAC and cured at 65°C for 7 days, was not clearly distinguished by the TG analyses since the dehydration of zeolitic type products also appeared within this temperature range (60 - 160°C) [29]. The alkali-activated gel band progressively broadened with increasing CAC contents, which is attributed to a different composition of the newly-formed gel. The pastes containing 50 wt.% CAC exhibited a double peak in this region, which denotes the overlapping dehydration processes of different calcium aluminum silicate hydrates. No signals attributed to carbonates were identified by the TG analyses since, according to Hidalgo et al. [13], bands appear within the 625°C to 875°C temperature range.

In good agreement with the XRD results, the signal originated by the C_3AH_6 phase (≈ 340 °C) [16] was clearly identified only in the activated pastes containing 30 wt.% and 50 wt.% CAC cured at 65°C, which showed increasing intensity with more CAC contents. Although a slight deviation within this range appeared in the DTG curve for the 50 wt.% CAC blended paste cured at 20°C, the XRD analyses did not clearly distinguish the cubic phase in this sample.

1
2 **3.6. Scanning electron microscopy (SEM)**
3
4
5
6
7

8 The SEM micrographs of the alkali-activated RCBW-CAC blends containing 10 wt.% and 50
9 wt.% CAC, cured at 20°C for 28 days and at 65°C for 7 days, are shown in Fig. 6. A denser
10 microstructure was observed with increasing CAC contents, which is in good agreement with
11 the compressive strength results. Although no cubic hydrates were clearly identified by the
12 FTIR, XRD or TG analyses in the samples containing 10 wt.% CAC, minor amounts of this
13 phase were observed by SEM. Despite a most particular microstructure having developed in the
14 blended pastes containing 50 wt.% CAC and cured at 65°C, no mortars with this amount of CAC
15 were obtained since rapid setting occurred in the preparation process.
16
17
18
19
20
21
22
23
24
25
26
27

28 **4. Conclusions**
29
30
31
32
33
34

35 An alternative cementitious system has been developed at both room temperature and 65°C by
36 the alkali activation of red clay brick waste in the presence of calcium aluminate cement. The
37 conclusions drawn according to the results of this paper are listed below.
38
39
40
41
42

43 - Addition of calcium aluminate cement accelerates the alkali-activation process of red clay brick
44 waste, which is particularly important for the mortars cured at room temperature. While up to 50
45 MPa were obtained under compression after 3 curing days at 20°C with 40 wt.% CAC, similar
46 compressive strength values were obtained in the mortars that contained 20 wt.% CAC after 28
47 curing days.
48
49
50
51
52

53 - Compressive strength values increased with CAC addition, curing temperature and curing
54 time. Although the mortars that contained 50 wt% CAC rapidly set and could not be prepared,
55 up to 92 MPa were obtained in the blend with 40 wt.% CAC that was cured at 65°C for 7 days .
56
57
58
59
60
61
62
63
64
65

1 - The main reaction product was a cementitious gel containing Ca and Al from CAC. CAC did
2 not undergo normal hydration and, while the cubic phase C_3AH_6 was identified only in the
3
4 pastes containing the largest CAC amounts (30 wt.% and 50 wt.%) cured at 65°C, bayerite was
5 distinguished only in the system with 50 wt.% CAC (65°C). Thus the typical durability problems
6 associated with CAC hydrates (conversion, carbonation, alkaline hydrolysis) are not expected in
7 the alkali-activated RCBW/CAC systems blended with up to 20 wt.% CAC, no matter what the
8 curing temperature may be.
9
10
11
12
13
14
15
16
17
18
19

20 **Acknowledgements**

21
22
23
24
25
26 The authors are grateful to the Spanish Ministry of Science and Innovation for supporting this
27 study through Project GEOCEDEM BIA 2011-26947, and to FEDER funding.
28
29
30
31
32
33

34 **References**

- 35
36
37
38
39
40 [1] Juenger MCG, Winnefeld F, Provis JL, Ideker JH. Advances in alternative cementitious
41 binders. *Cem Concr Res* 2011;41:1232–1243.
42
43
44
45
46 [2] Shi C, Fernández-Jiménez A, Palomo A. New cements for the 21st century: The pursuit of
47 an alternative to Portland cement. *Cem Concr Res* 2011;41:750–763.
48
49
50
51
52 [3] Tashima MM, Akasaki JL, Castaldelli VN, Soriano L, Monzó J, Payá J, Borrachero MV. New
53 geopolymeric binder based on fluid catalytic cracking catalyst residue (FCC). *Mater Lett*
54 2012;80:50–52.
55
56
57
58
59
60
61
62
63
64
65

1
2 [4] Redden R, Neithalath N. Microstructure, strength, and moisture stability of alkali activated
3 glass powder-based binders. *Cem Concr Compos* 2014;45:46-56.

4
5
6 [5] Gluth GJG, Lehmann C, Rübner K, Kühne HC. Reaction products and strength development
7 of wastepaper sludge ash and the influence of alkalis. *Cem Concr Compos* 2014;45:82-88.

8
9
10
11 [6] Puertas F, Barba A, Gazulla MF, Gómez MP, Palacios M, Martínez-Ramírez S. Ceramic
12 wastes as raw materials in portland cement clinker fabrication: characterization and alkaline
13 activation. *Mater Construcc* 2006;56(281):73-84.

14
15
16 [7] Payá J, Borrachero MV, Monzó J, Soriano L, Tashima MM. A new geopolymetric binder from
17 hydrated-carbonated cement. *Mater Lett* 2012;74:223-225.

18
19
20 [8] Reig L, Soriano L, Borrachero MV, Monzó J, Payá J. Influence of the activator concentration
21 and calcium hydroxide addition on the properties of alkali-activated porcelain stoneware. *Constr*
22 *Build Mater* 2014;63:214–222.

23
24
25 [9] Reig L, Tashima MM, Borrachero MV, Monzó J, Cheeseman CR, Payá J. Properties and
26 microstructure of alkali-activated red clay brick waste. *Constr Build Mater* 2013;43:98–106.

27
28
29 [10] Fernández-Jiménez A, Palomo A, Vazquez T, Vallepu R, Terai T, Ikeda K. Alkaline
30 activation of blends of metakaolin and calcium aluminate. *J Am Ceram Soc* 2008;91(4):1231–
31 1236.

32
33
34 [11] Arbi K, Palomo A, Fernández-Jiménez A. Alkali-activated blends of calcium aluminate
35 cement and slag/diatomite. *Ceram Int* 2013;39:9237–9245.

36
37
38 [12] Pacewska B, Nowacka M, Antonovic V, Aleknevičius M. Investigation of early hydration of
39 high aluminate cement-based binder at different ambient temperatures. *J Therm Anal Calorim*
40 2012;109:717–726.

- 1
2 [13] Hidalgo A, García JL, Alonso MC, Fernández L, Andrade C. Microstructure development in
3 mixes of calcium aluminate cement with silica fume or fly ash. *J Therm Anal Calorim*
4 2009;96(2):335–345.
5
6
7
8
9
10 [14] Giner-Juan FJ. Carbonatación vs. Aluminosis. In: Proceedings of the 'V Convención
11 Técnica y Tecnológica de la Arquitectura Técnica', ContART 2009, Albacete-Spain, March,
12 2009. p. 25-27.
13
14
15
16
17 [15] Rivas-Mercury JM, de Aza AH, Turrillas X, Pena P. Hidratación de los cementos de
18 aluminatos de calcio (Parte I). *Bol Soc Esp Cerám Vidrio* 2003;42(5):269-276.
19
20
21
22
23 [16] Pacewska B, Nowacka M, Wilinska I, Kubissa W, Antonovich V. Studies on the influence of
24 spent FCC catalyst on hydration of calcium aluminate cements at ambient temperature. *J Therm*
25 *Anal Calorim* 2011;105:129–140.
26
27
28
29
30
31 [17] Pastor C, Fernández-Jiménez A, Vázquez T, Palomo A. Calcium aluminate cement
32 hydration in a high alkalinity environment. *Mater Construcc* 2009;59(293):21-34.
33
34
35
36
37 [18] Fernández-Jiménez A, Vázquez T, Palomo A. Effect of sodium silicate on calcium
38 aluminate cement hydration in highly alkaline media: a microestructural characterization. *J Am*
39 *Ceram Soc* 2011;94(4):1297–1303.
40
41
42
43
44 [19] Reig L, Tashima MM, Soriano L, Borrachero MV, Monzó J, Payá J. Alkaline activation of
45 ceramic waste materials. *Waste Biomass Valor* 2013;4(4):729–736.
46
47
48
49
50 [20] García-Lodeiro I, Maltseva O, Palomo A, Fernández-Jiménez A. Hybrid alkaline cements.
51 Part I: Fundamentals. *Rom J Mater* 2012;42(4):330-335.
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 [21] Fernández-Carrasco L, Vázquez E. Reactions of fly ash with calcium aluminate cement and
2 calcium sulphate. *Fuel* 2009;88:1533–1538.

3
4
5
6 [22] Fernández-Carrasco L, Torréns-Martín D, Martínez-Ramírez S. Carbonation of ternary
7 building cementing materials. *Cem Concr Compos* 2012;34:1180–1186.

8
9
10
11 [23] Pacewska B, Nowacka M, Antonovic V, Aleknevičius M. Investigation of early hydration of
12 high aluminate cement-based binder at different ambient temperatures. *J Therm Anal Calorim*
13 2012;109:717–726.

14
15
16
17 [24] Fernández-Carrasco L, Vázquez T. Aplicación de la espectroscopia infrarroja al estudio de
18 cemento aluminoso. *Mater Construcc* 1996;46(241):53-65.

19
20 [25] Hajimohammadi A, Provis JL, van Deventer JSJ. The effect of silica availability on the
21 mechanism of geopolymerisation. *Cem Concr Res* 2011;41:210–216.

22
23
24
25 [26] Garcia-Lodeiro I, Palomo A, Fernández-Jiménez A, Macphee D.E. Compatibility studies
26 between N-A-S-H and C-A-S-H gels. Study in the ternary diagram $\text{Na}_2\text{O}-\text{CaO}-\text{Al}_2\text{O}_3-\text{SiO}_2-$
27 H_2O . *Cem Concr Res* 2011;41:923–931.

28
29
30
31 [27] García-Lodeiro I, Fernández-Jiménez A, Palomo A. Variation in hybrid cements over time.
32 Alkaline activation of fly ash–Portland cement blends. *Cem Concr Res* 2013;52:112–122.

33
34
35 [28] Granizo ML, Alonso S, Blanco-Varela MT, Palomo A. Alkaline activation of metakaolin:
36 effect of calcium hydroxide in the products of reaction. *J Am Ceram Soc* 2002;85(1):225–31.

37
38
39
40 [29] Bernal SA, Gutierrez RM, Provis JL, Rose V. Effect of silicate modulus and metakaolin
41 incorporation on the carbonation of alkali silicate-activated slags. *Cem Concr Res* 2010;40:898–
42 907.

LIST OF FIGURES:

1
2
3
4 Fig. 1. SEM image of: a) Ground RCBW; b) CAC cement
5
6

7
8 Fig. 2. Influence of CAC addition and curing conditions on the compressive strength of the
9
10 alkali-activated RCBW-CAC mortars cured at 20°C and 65°C.
11
12

13
14 Fig. 3. FTIR spectra for the alkali-activated RCBW-CAC blends and the hydrated CAC paste,
15
16 cured at: a) 20°C for 28 days; b) 65°C for 7 days.
17
18


19
20 Fig. 4. X-ray diffractograms for the alkali-activated RCBW-CAC blends and the water-hydrated
21
22 CAC paste, cured at: a) 20°C for 28 days; b) 65°C for 7 days. Q=Quartz (SiO_2); A=Albite
23
24 ($\text{NaAlSi}_3\text{O}_8$); m=microcline (KAlSi_3O_8); R=rankinite ($2\text{SiO}_2 \cdot 3\text{CaO}$); M=monocalcium aluminate,
25
26 CA ($\text{CaO} \cdot \text{Al}_2\text{O}_3$); D= CAH_{10} ($\text{CaAl}_2\text{O}_4 \cdot 10\text{H}_2\text{O}$); O= C_2AH_8 ($\text{Ca}_2\text{Al}_2\text{O}_5 \cdot 8\text{H}_2\text{O}$); K=katoite, C_3AH_6
27
28 ($\text{Ca}_3\text{Al}_2\text{O}_6 \cdot 6\text{H}_2\text{O}$); G=gibbsite ($\text{Al}(\text{OH})_3$); B=bayerite ($\text{Al}(\text{OH})_3$); S=Linde A, $\text{Ca}_6(\text{AlSiO}_4)_{12} \cdot 30\text{H}_2\text{O}$;
29
30 AL=carboaluminate ($\text{Ca}_4\text{Al}_2\text{O}_6\text{CO}_3 \cdot 11\text{H}_2\text{O}$); C=aluminohydrocalcite ($\text{CaAl}_2(\text{CO}_3)_2(\text{OH})_4 \cdot 3\text{H}_2\text{O}$);
31
32 H=Herschelite ($\text{NaAlSi}_2\text{O}_6 \cdot 3\text{H}_2\text{O}$).
33
34
35

36
37 Fig. 5. Differential thermogravimetric curves for the alkali-activated RCBW-CAC blends and a
38
39 hydrated CAC paste: a) cured at 20°C for 28 days; b) cured at 65°C for 7 days. Total mass loss
40
41 (as a %) within the 35-600°C range is indicated for each curve.
42
43

44
45 Fig. 6. Scanning electron microscope images of the alkali-activated RCBW-CAC blends cured at
46
47 20°C for 28 days and 65°C for 7 days.
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Figure

[Click here to download high resolution image](#)

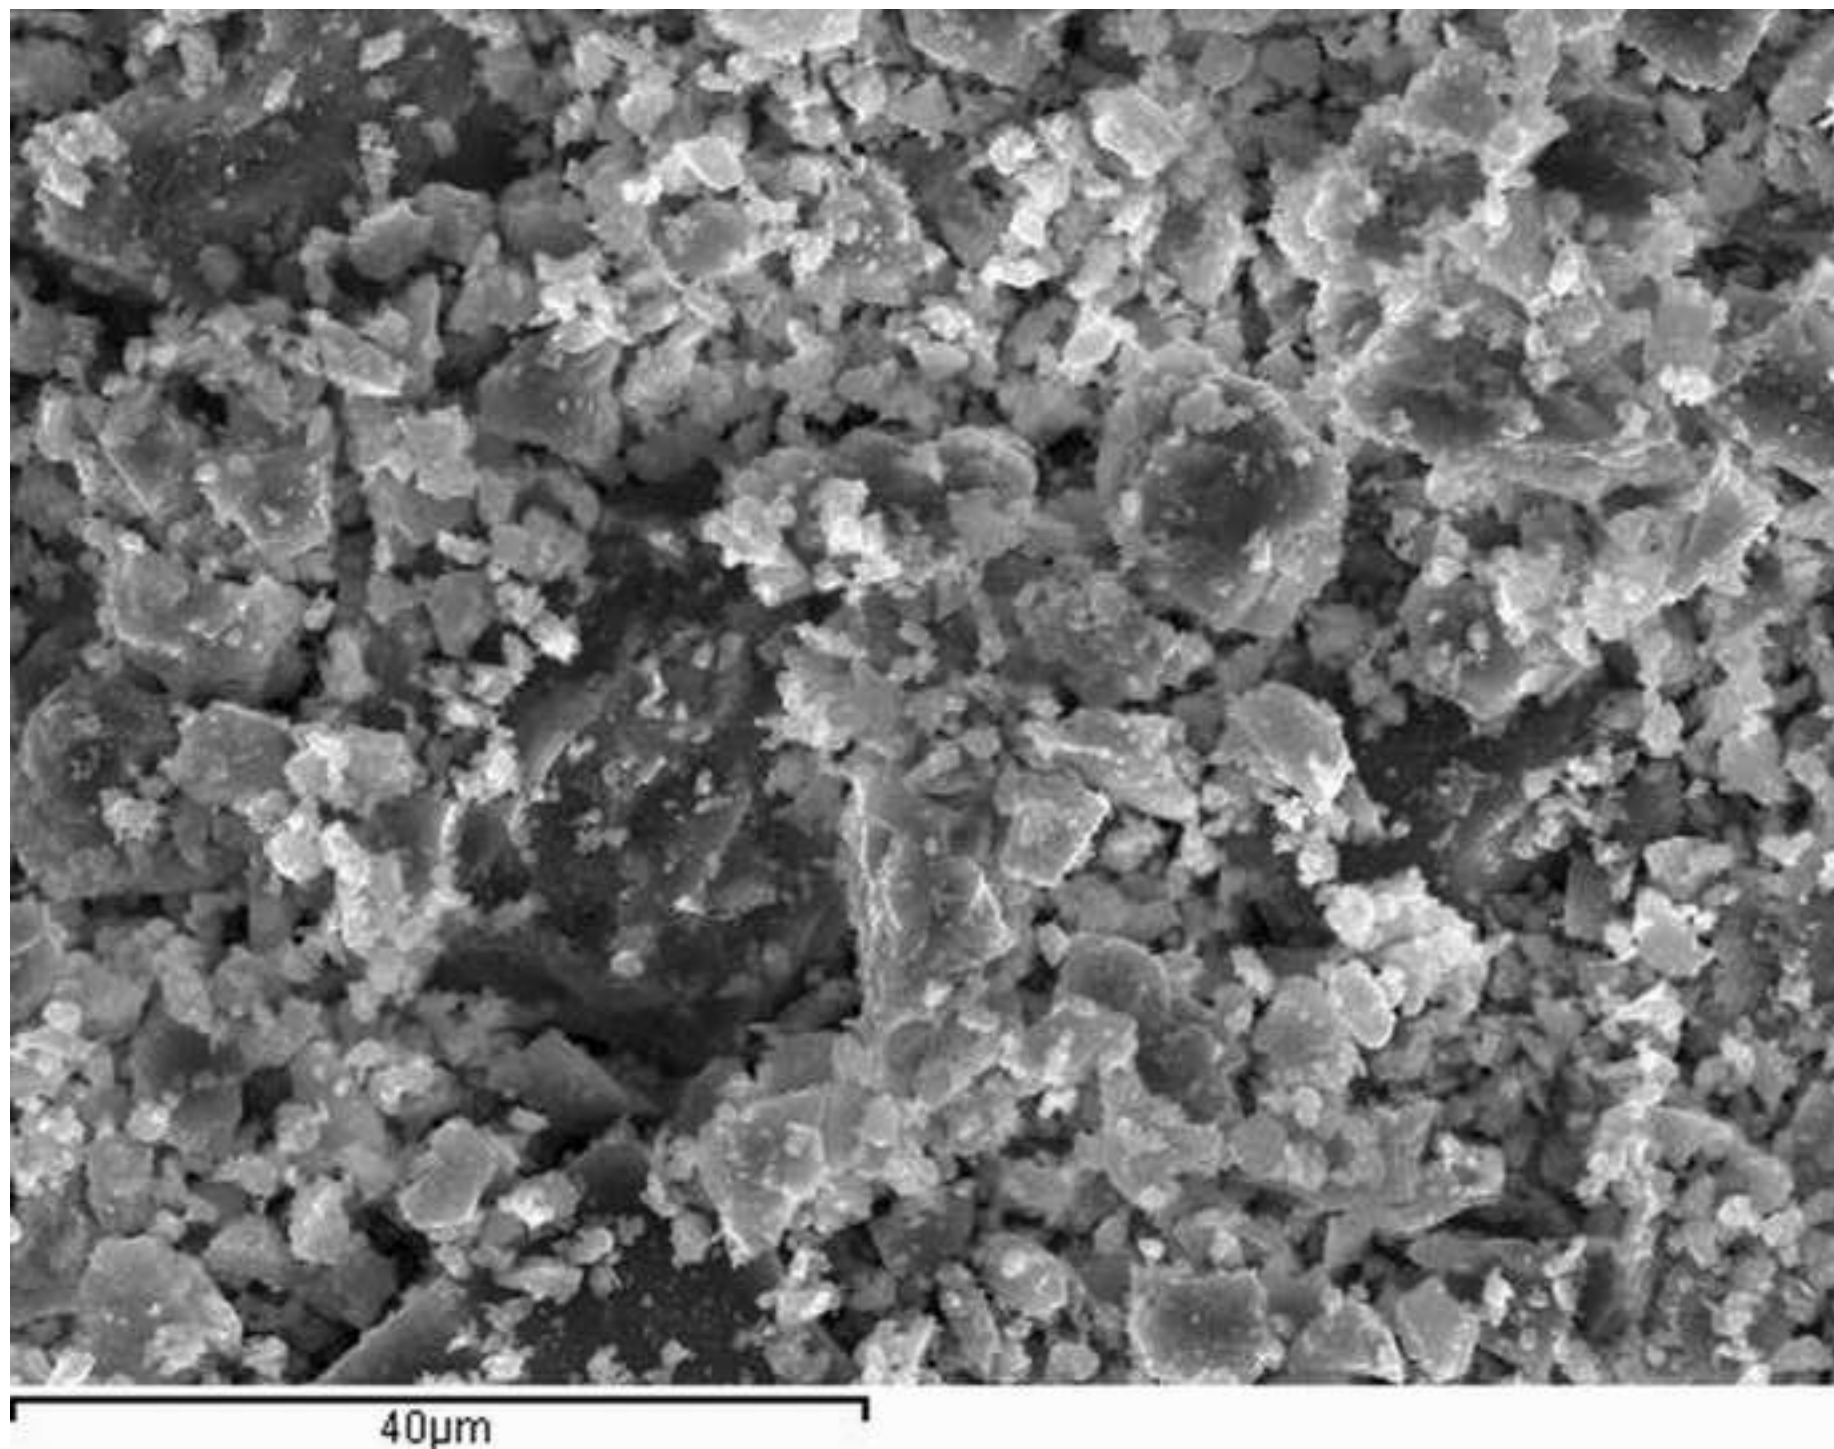

Figure

[Click here to download high resolution image](#)

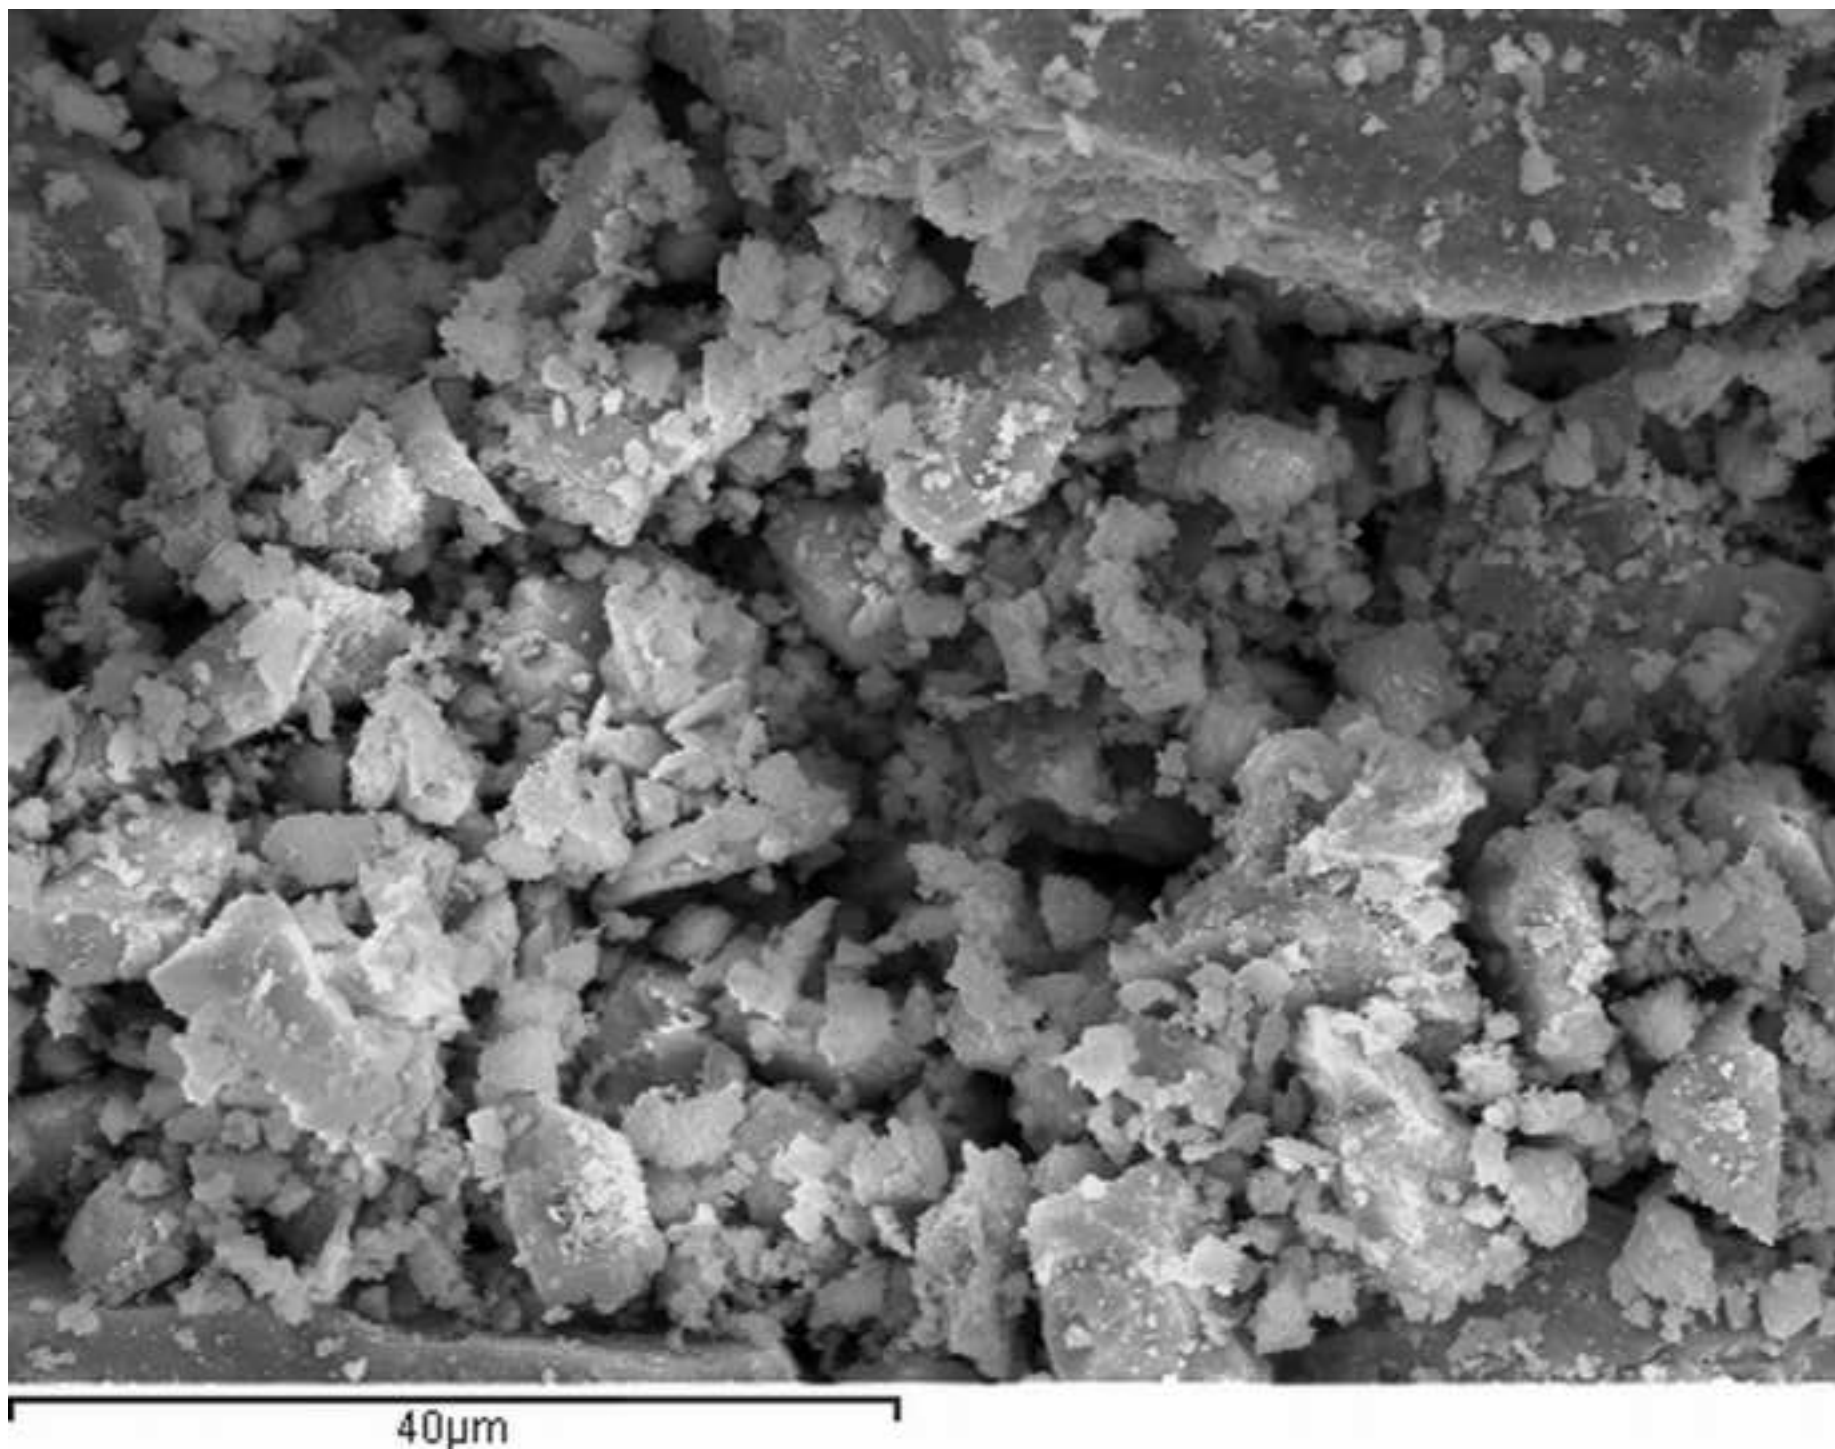


Figure
[Click here to download high resolution image](#)

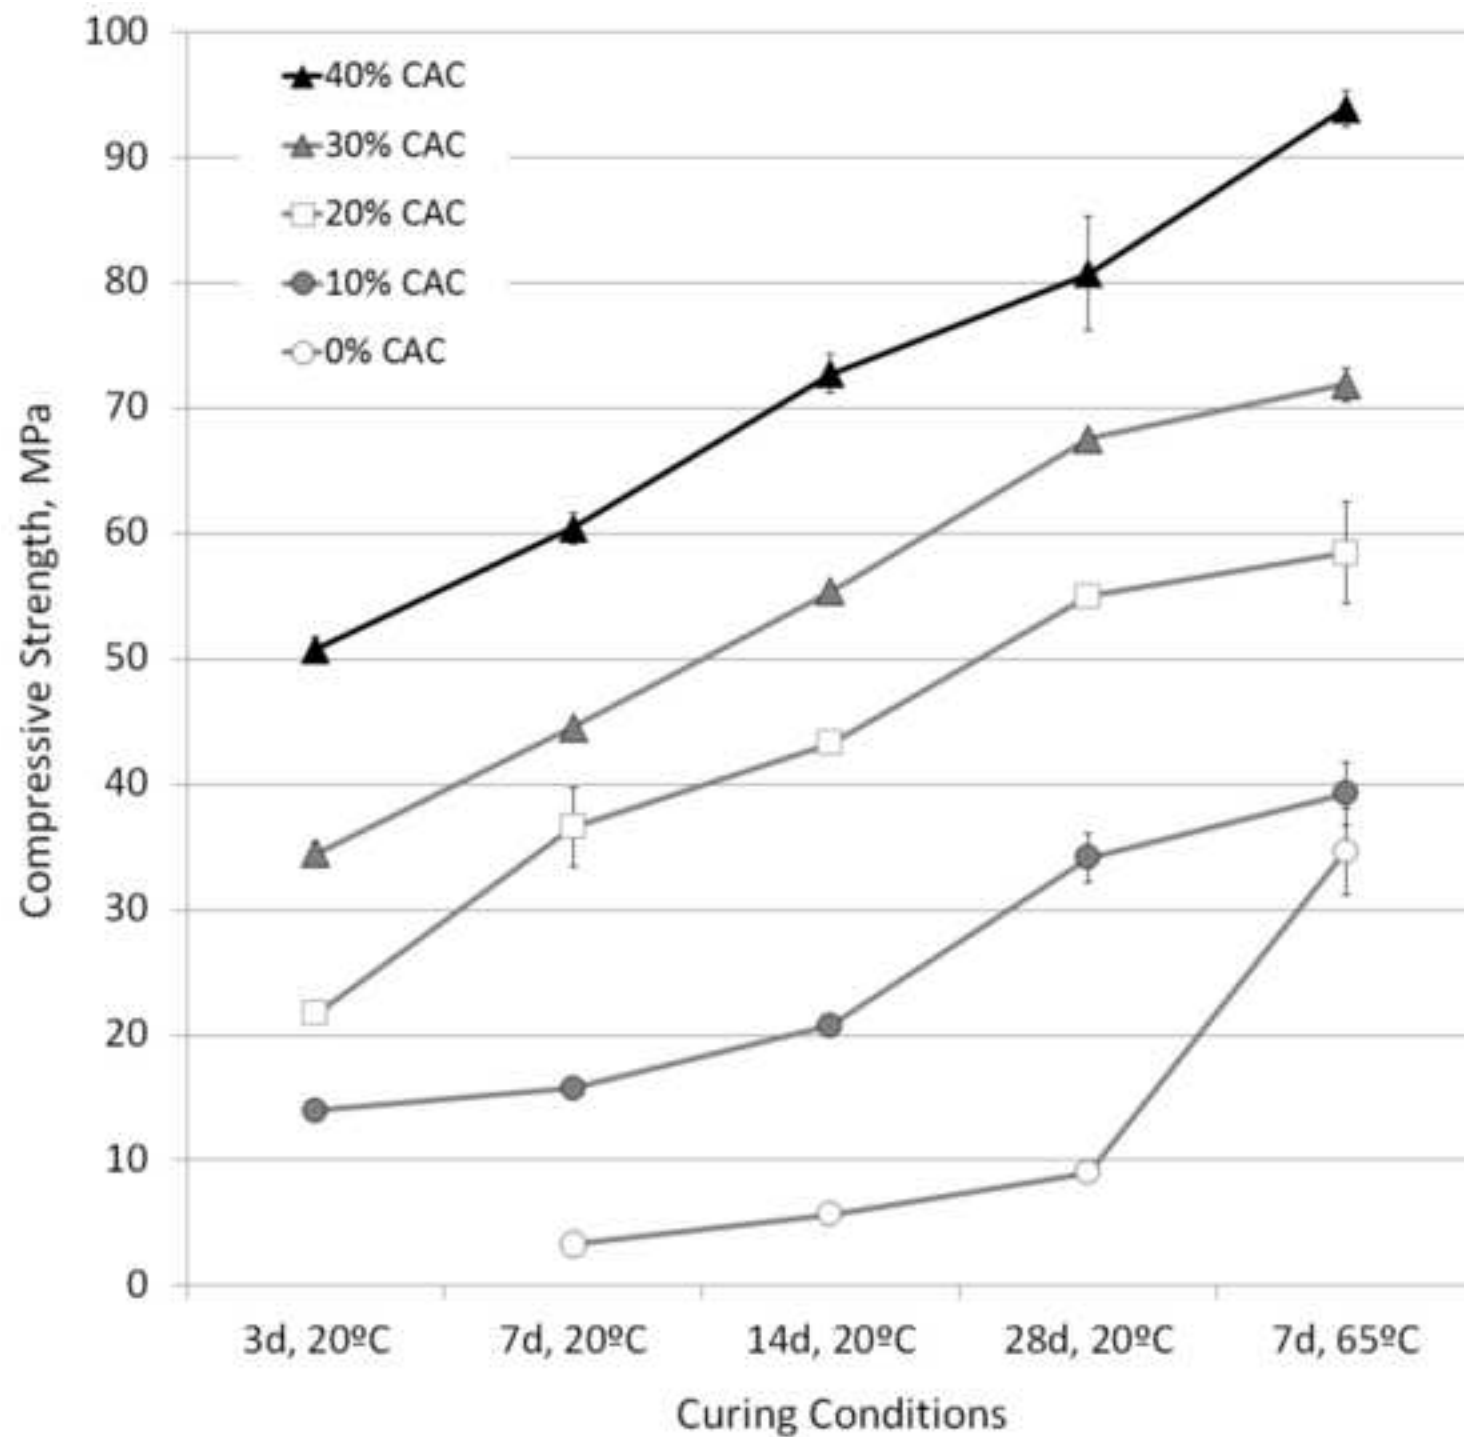


Figure
[Click here to download high resolution image](#)



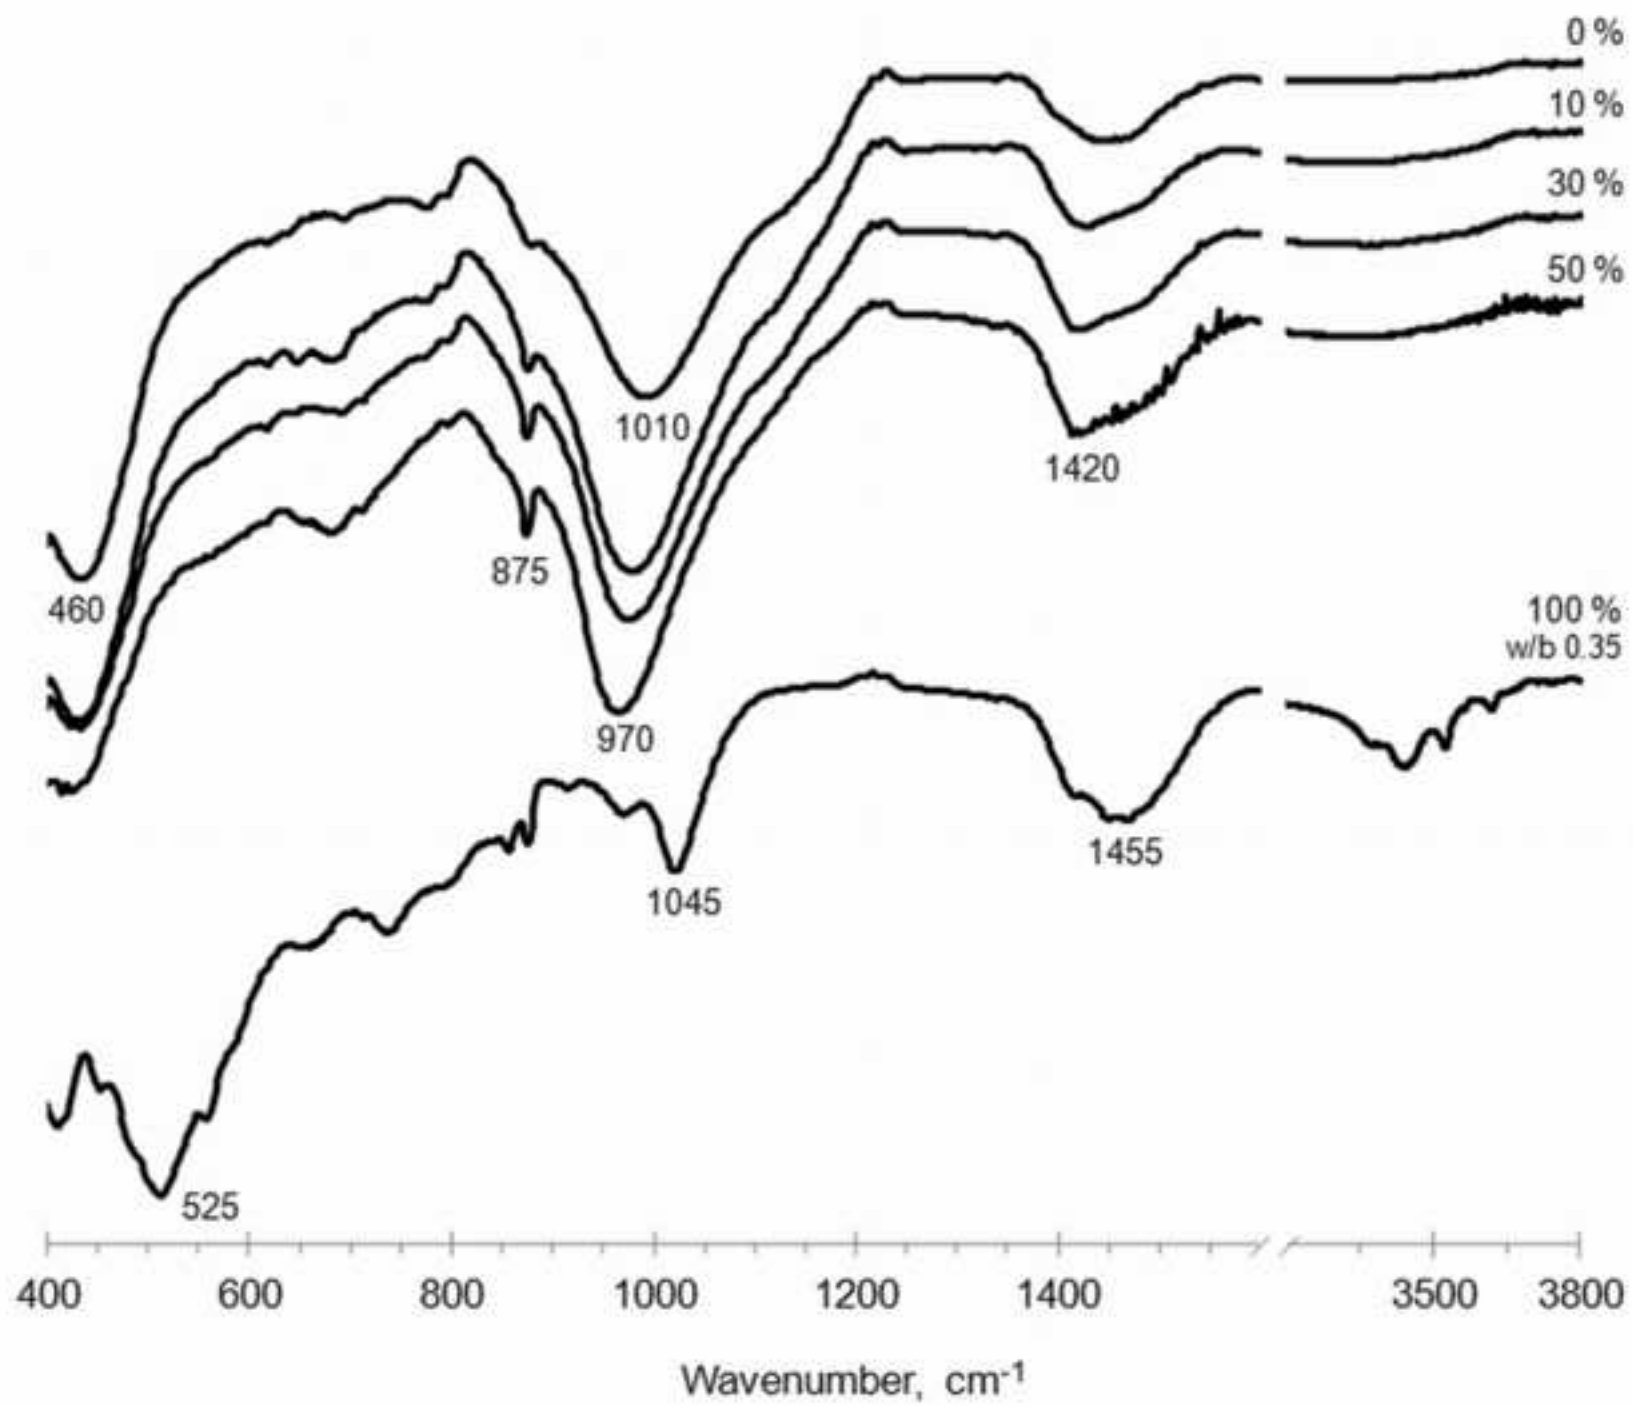


Figure
[Click here to download high resolution image](#)

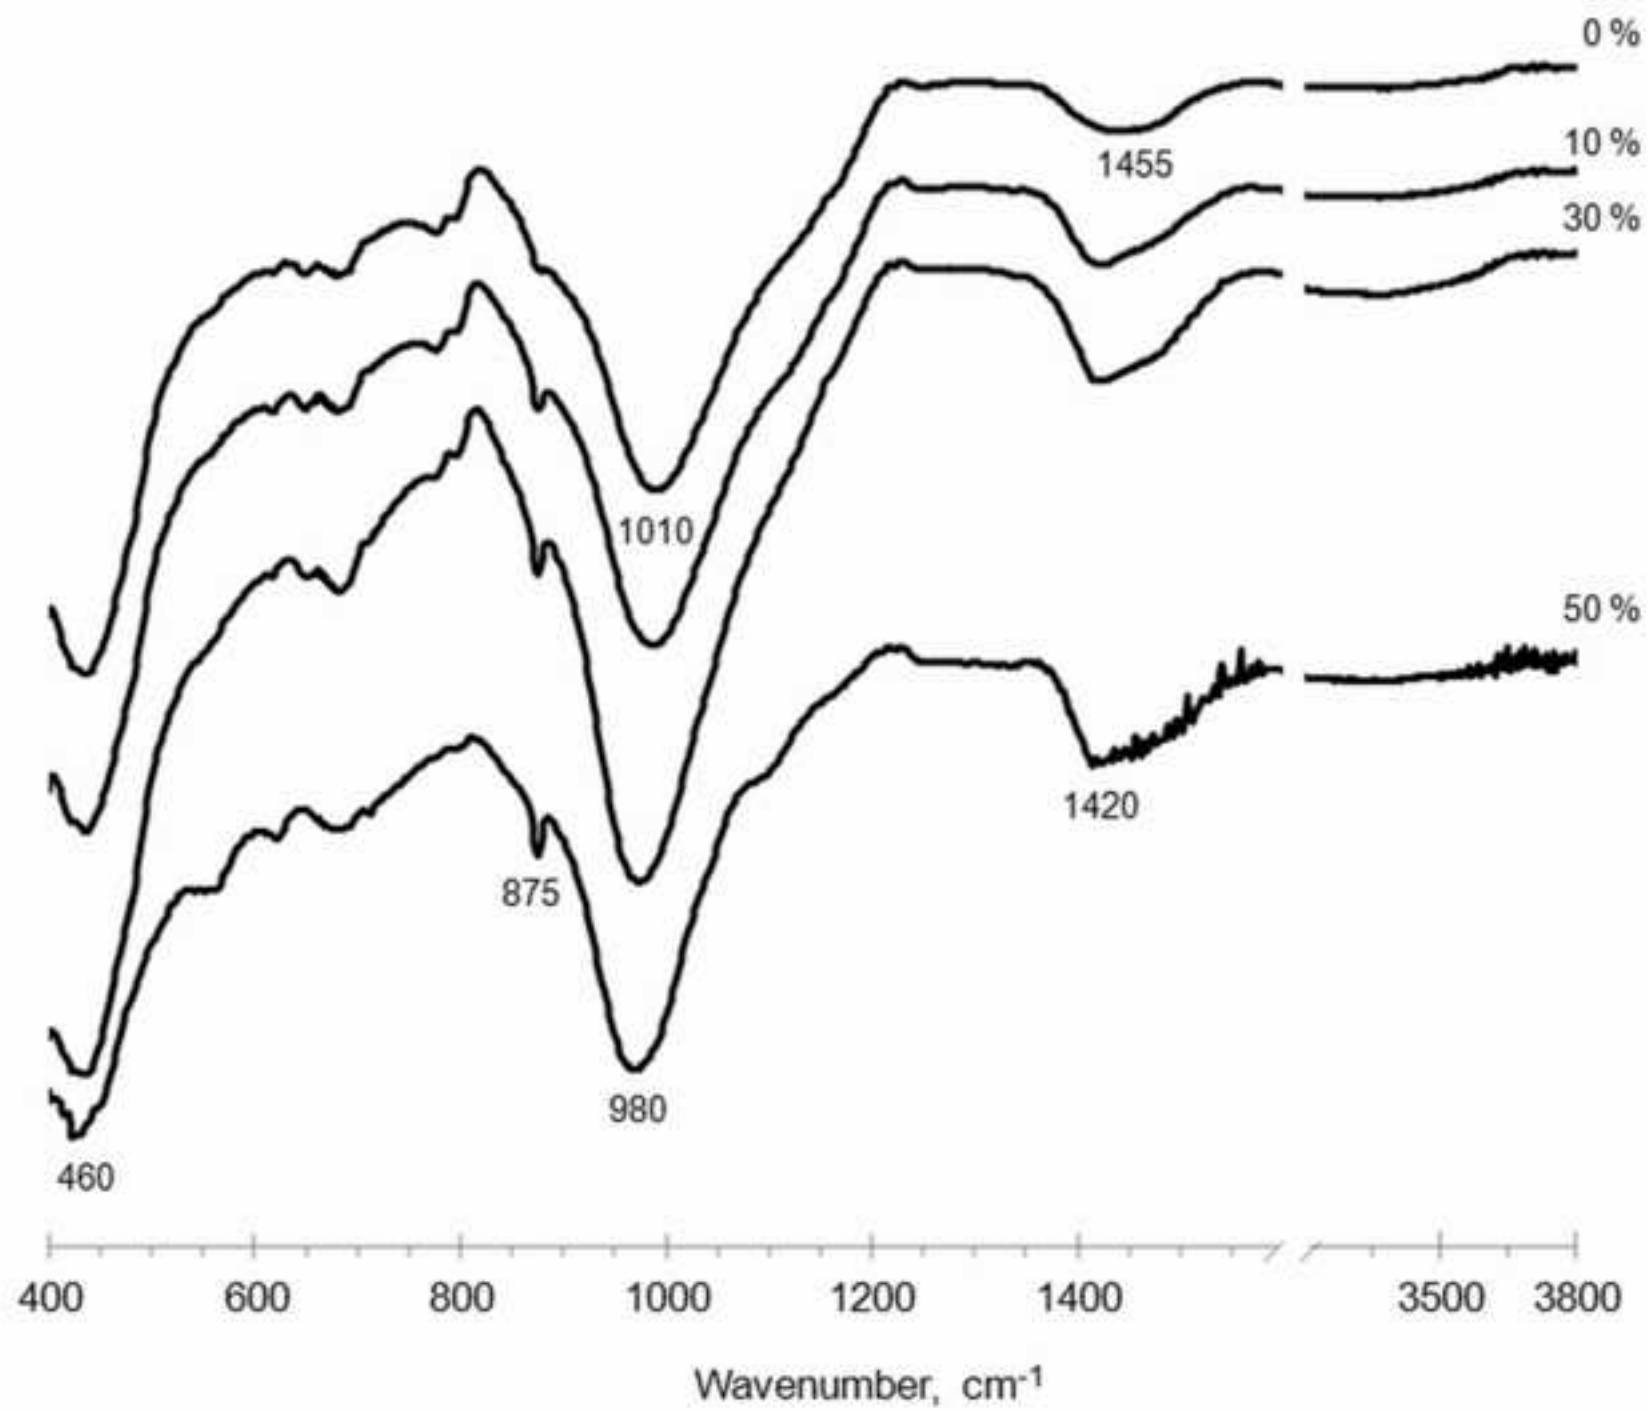

Figure

[Click here to download high resolution image](#)

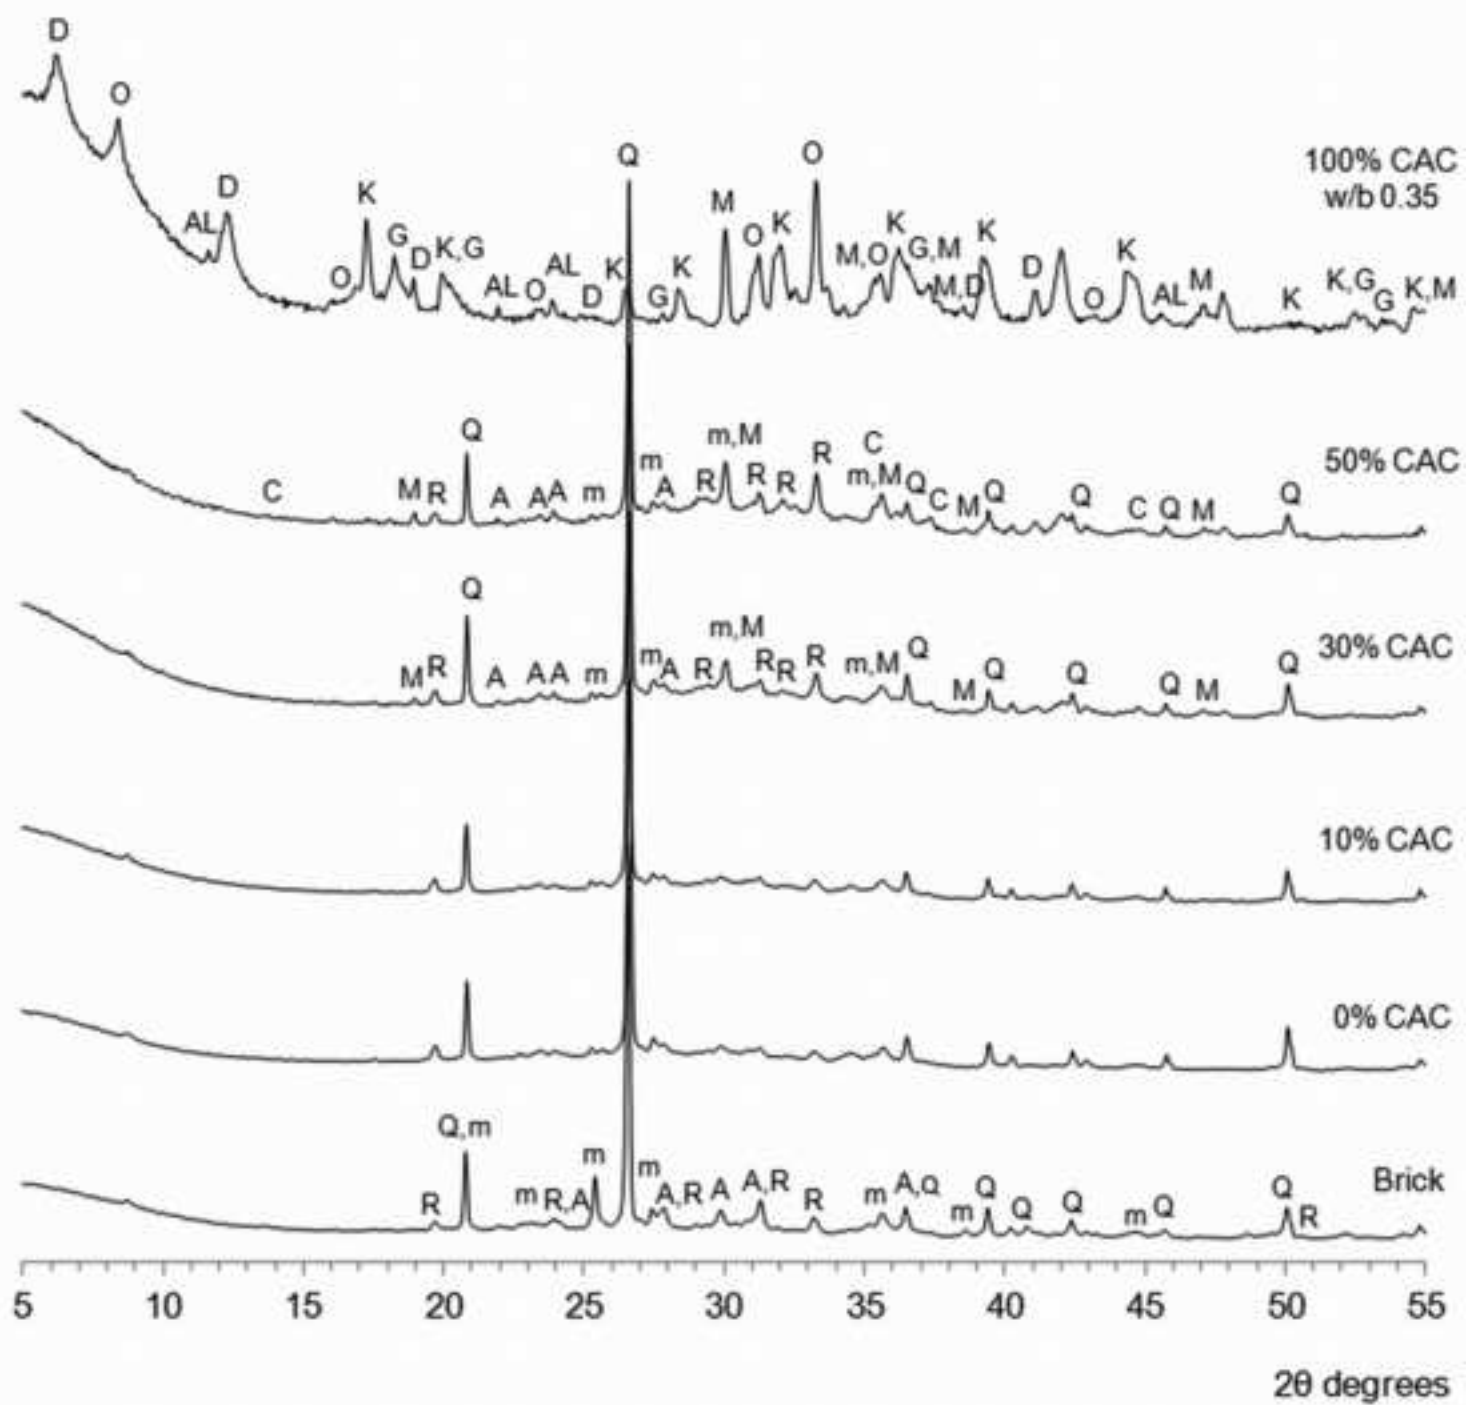

Figure

[Click here to download high resolution image](#)

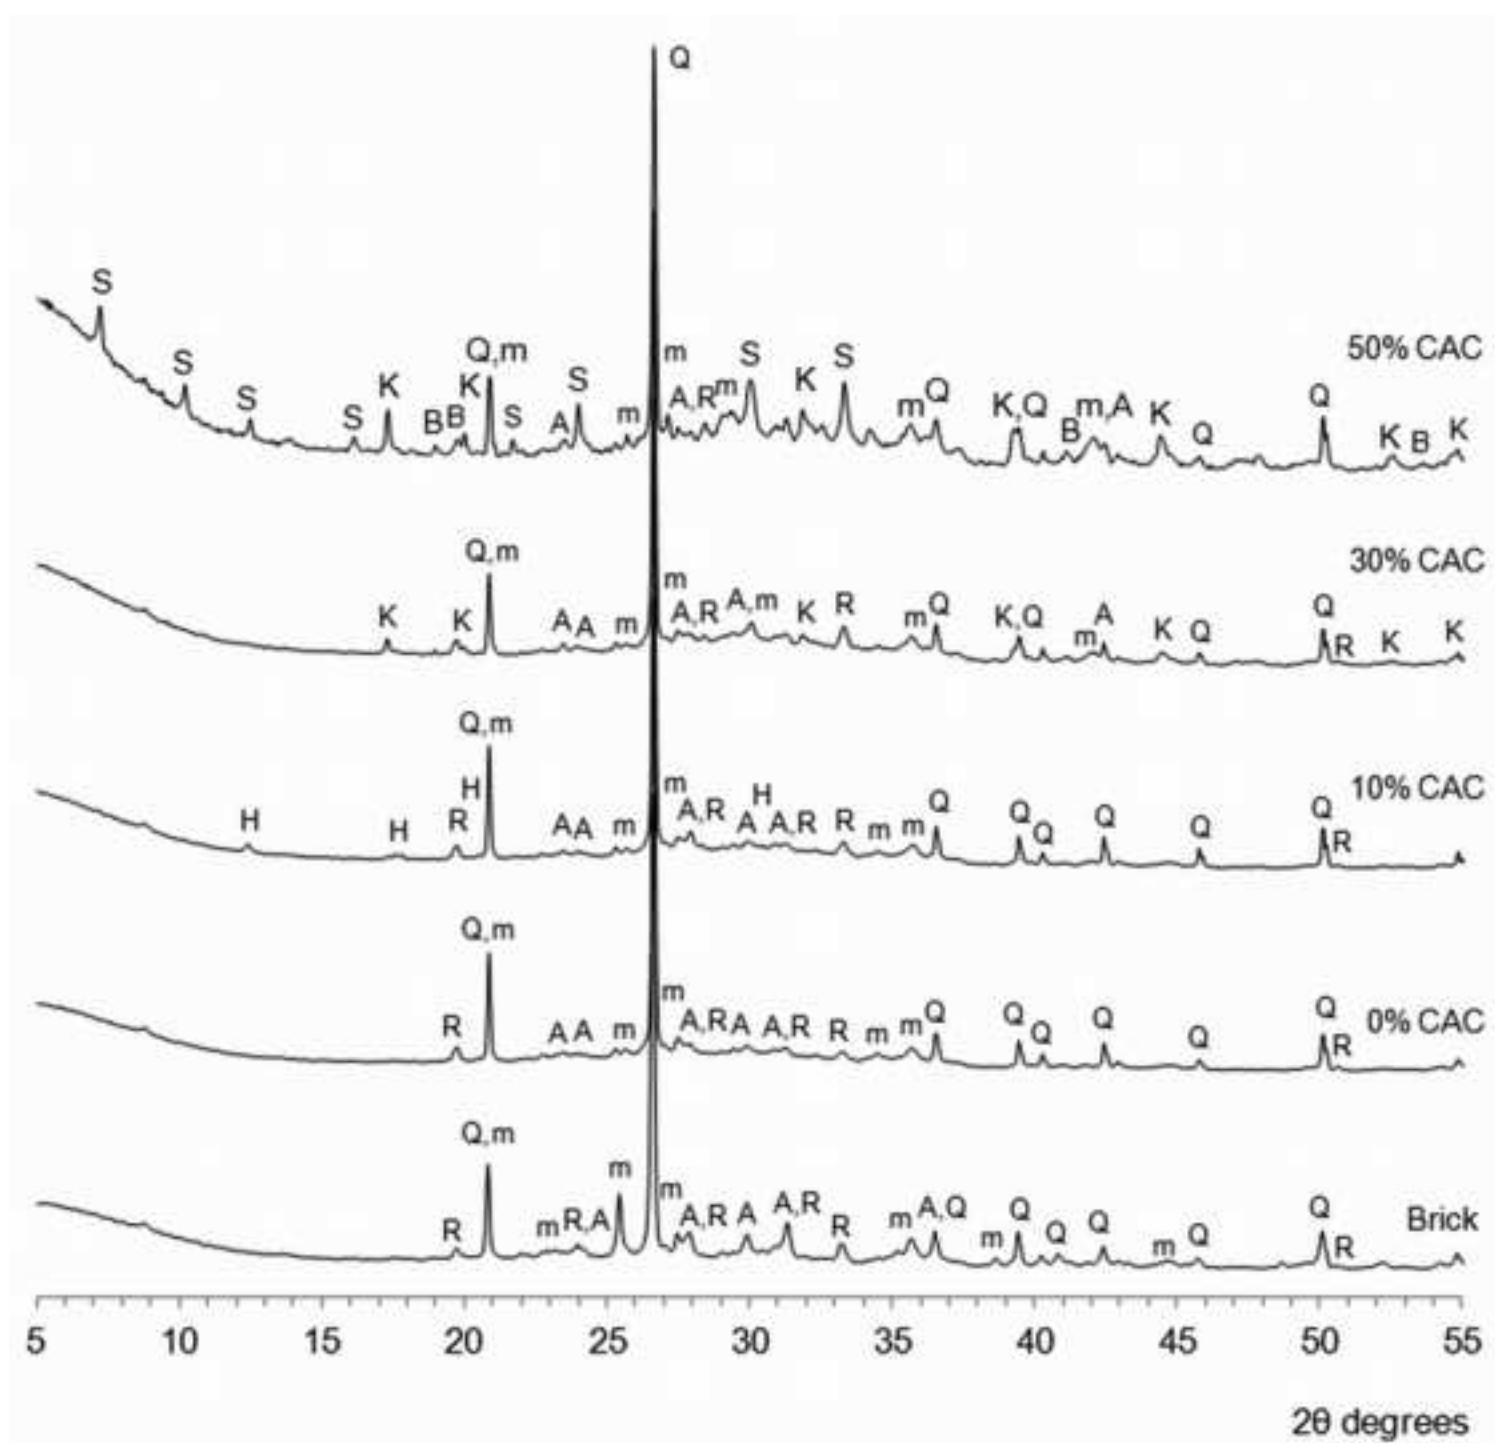


Figure
[Click here to download high resolution image](#)


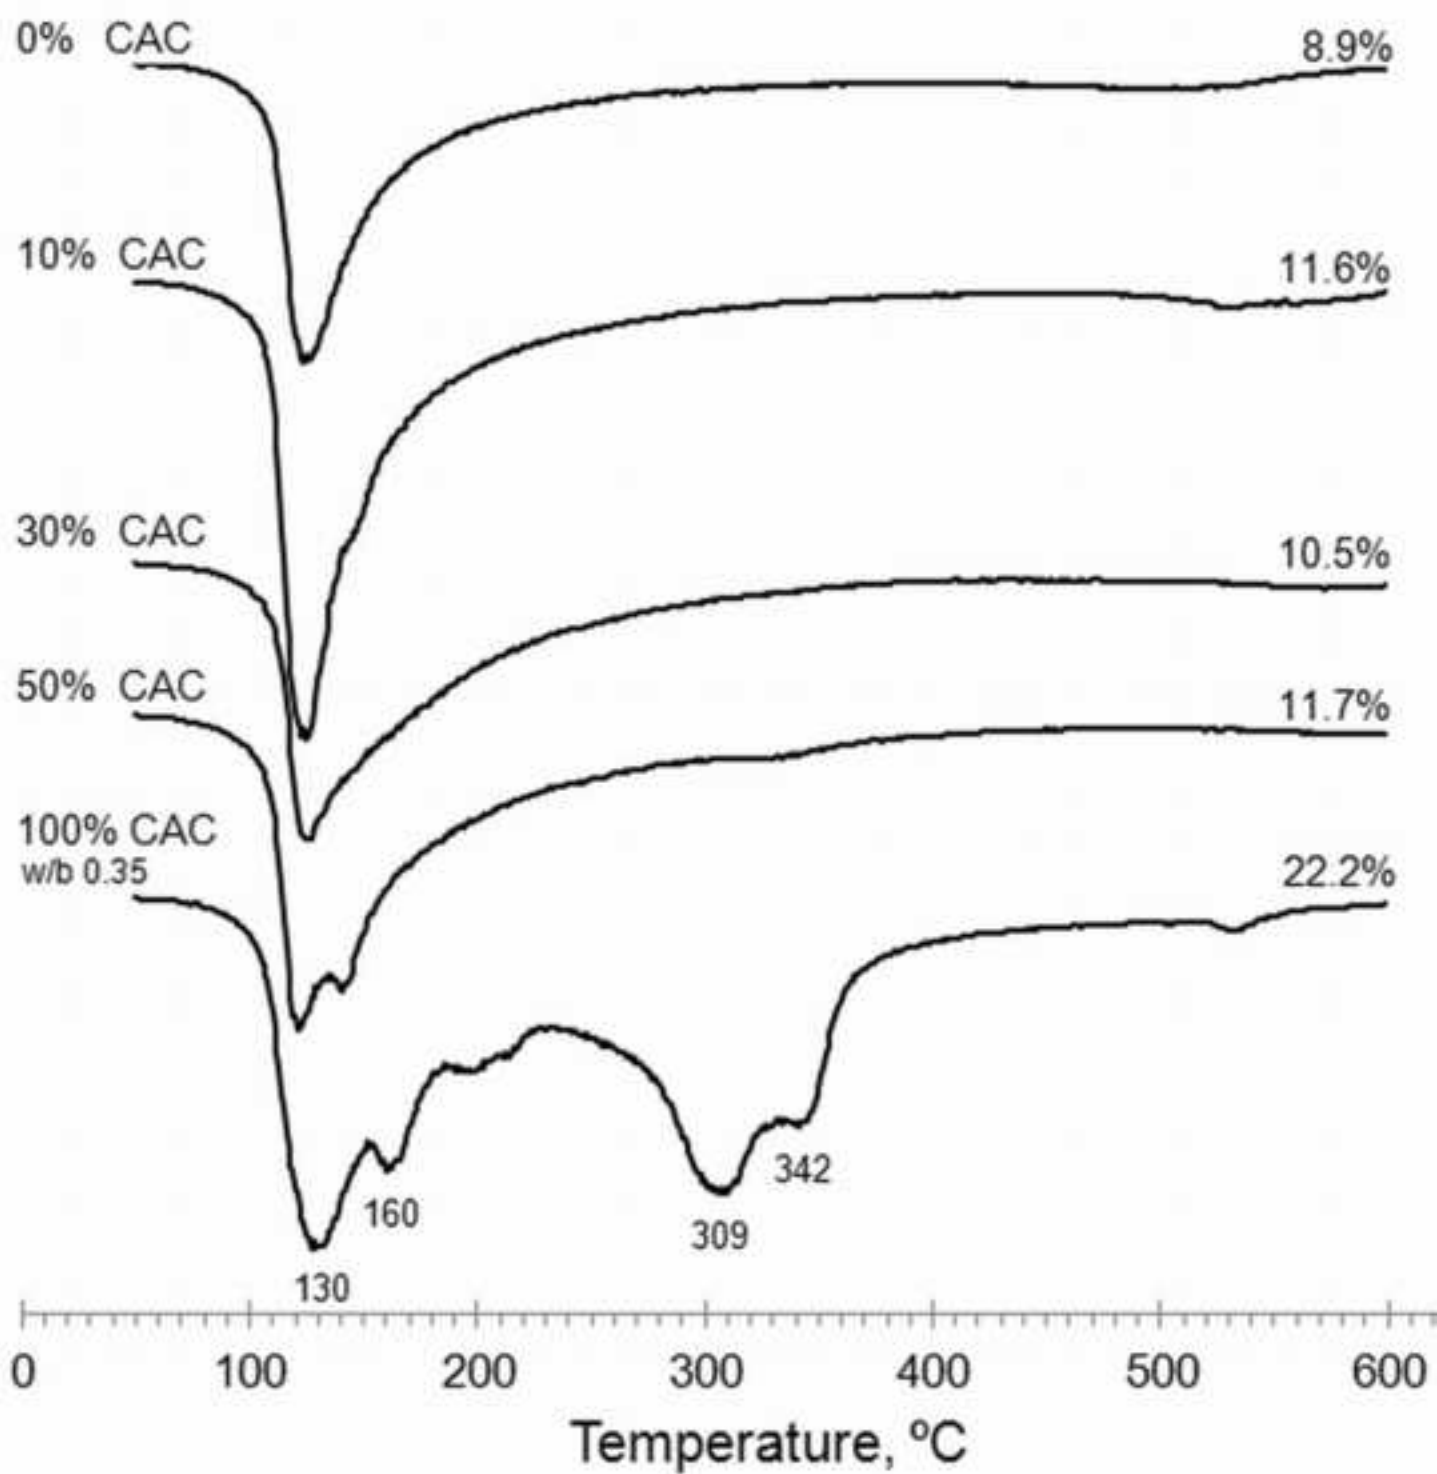


Figure
[Click here to download high resolution image](#)



Figure

[Click here to download high resolution image](#)

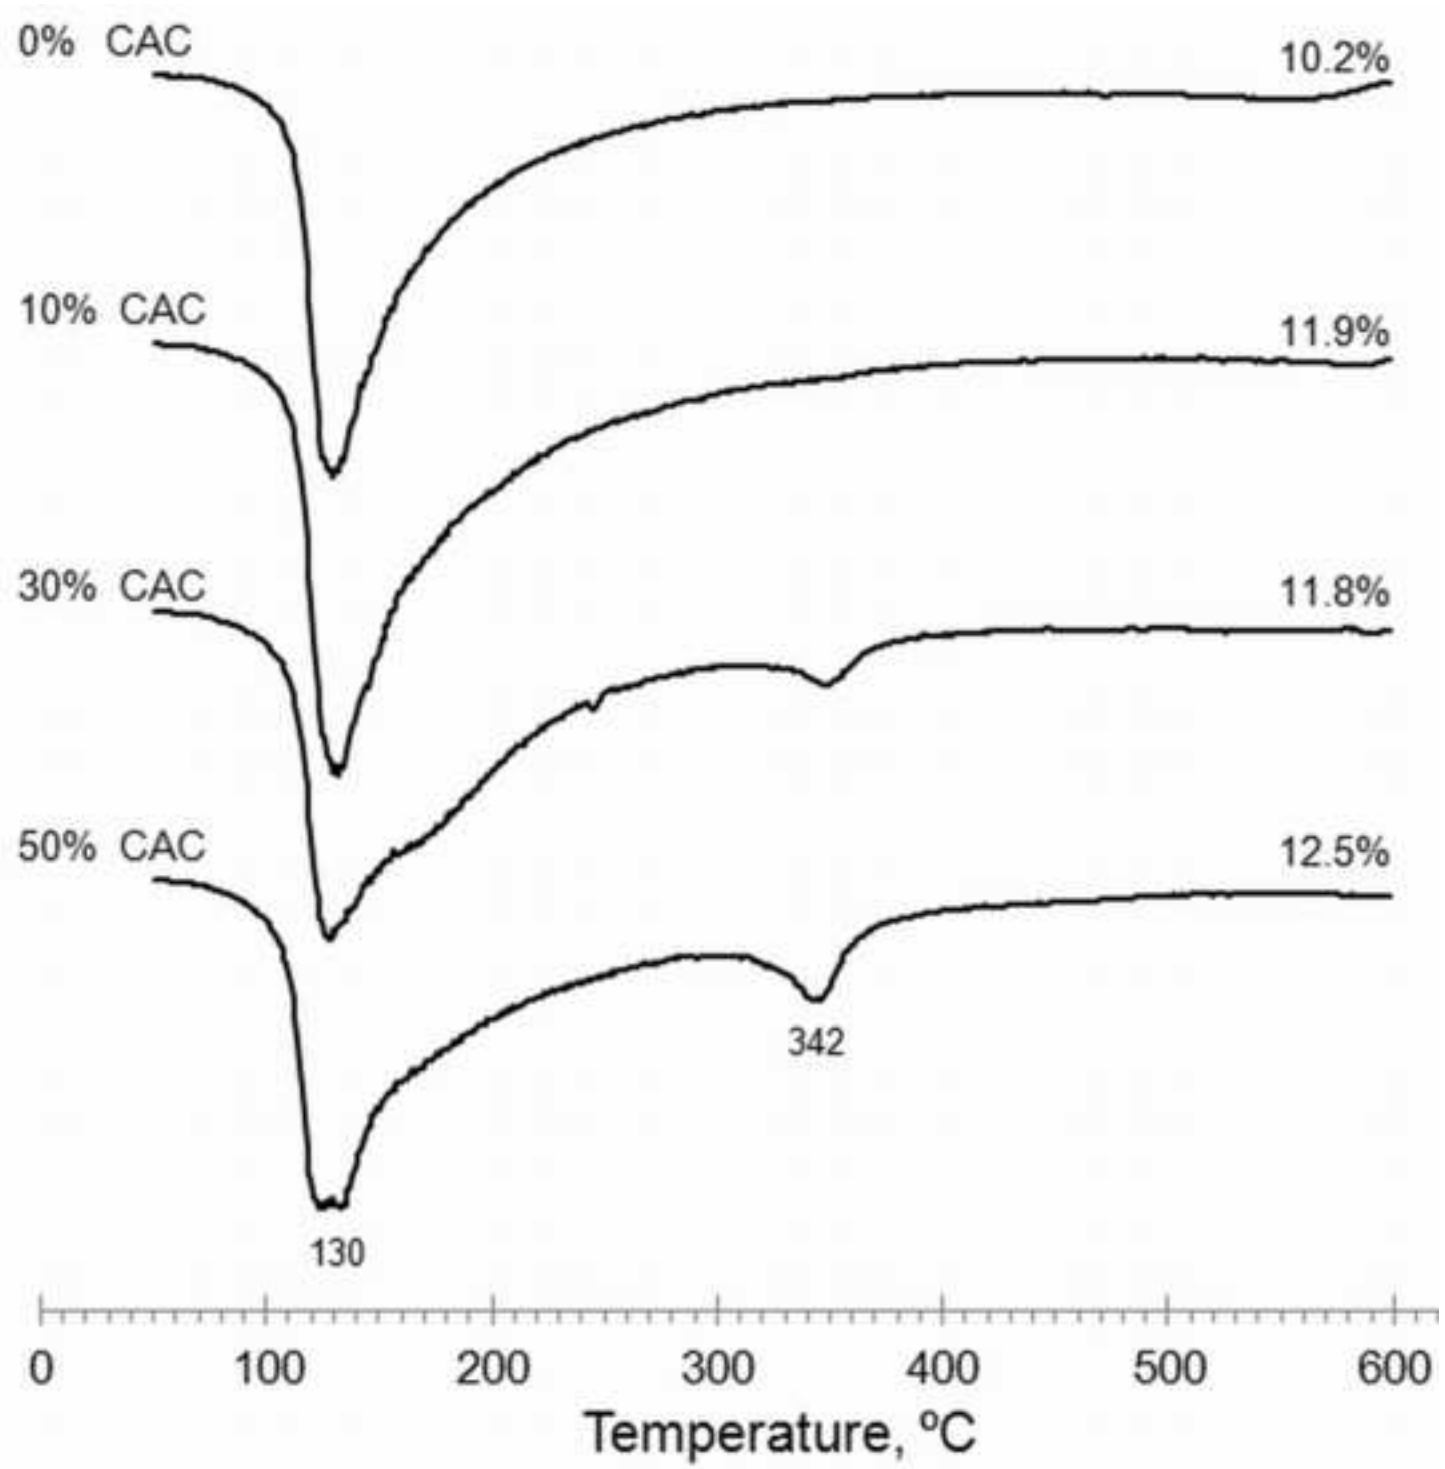